Hazardous compounds in recreational and urban recycled surfaces made from crumb rubber. Compliance with current regulation and future perspectives

Maria Celeiro [1], Daniel Armada [1], Thierry Dagnac [2], Jacob de Boer [3], Maria Llompart [1*]

[1] CRETUS Institute, Department of Analytical Chemistry, Nutrition and Food Science, Universidade de Santiago de Compostela, E-15782, Santiago de Compostela, Spain.

[2] Agronomic Research Centre (AGACAL-CIAM) – Unit of Organic Contaminants, Apartado 10, E-15080, A Coruña, Spain.

[3] Department of Environment and Health (E&H), Vrije Universiteit, De Boelelaan 1085, 1081 HV, Amsterdam, Netherlands.

* Corresponding author: Maria Llompart (e-mail: maria.llompart@usc.es; telephone: +34881814225; fax: +34881814468)

Field Code Changed

ABSTRACT

Crumb rubber obtained from scrap tires is greatly employed for the construction of different facilities for sport, recreational and other uses. However, in recent years the concern about their safety and the related adult~~s~~ and children exposure to these surfaces is growing. This study aims a thorough chemical characterization encompassing 42 hazardous compounds, including polycyclic aromatic hydrocarbons (PAHs), phthalates, adipates, antioxidants and vulcanization agents in a wide range of crumb rubber from different surfaces. For the extraction of the target compounds, a method based on ultrasound-assisted extraction followed by gas chromatography-tandem mass spectrometry (UAE-GC-MS/MS) has been validated. Forty crumb rubber samples coming from synthetic turf football pitches, outdoor and indoor playgrounds, urban pavements, commercial tiles and granulates, and scrap tires, were analyzed. In addition, green alternative materials, such as sand and artificial turf based on cork granulate infill were included to compare the levels of the target compounds with those of crumb rubber. Most of the analyzed recycled surfaces meet the recent limits proposed by the European Commission for rubber granulates and mulches, although they exceed in several cases the maximum levels allowed ~~by~~ for rubber consumer products. Besides, most of the other

target compounds, including several of them considered as endocrine disruptors, were detected in the analyzed samples, reaching parts per million concentrations.

KEYWORDS: Recycled rubber play surfaces; Public health; Polycyclic aromatic hydrocarbons, Hazardous organic compounds; Crumb rubber; Gas chromatography-tandem mass spectrometry

1. INTRODUCTION

The European Union (EU) is the second largest generator of scrap tires after United States, and according to the EU landfill and the end-of-life (EOL) vehicles directives, the national governments are obliged to address its recycling for safety, health and environmental purposes (Directive 2000/76/EC, Directive 2000/53/EC, Sebola et al. 2018).

The different processes and strategies proposed for the recycling of scrap (end-of-life) tires involve, among others, pyrolysis, controlled incineration, or mechanical crushing, the last one being the most employed one for its simplicity and low-cost. The obtained crumb rubber can be used in two different ways. Firstly, as infill in roads or sport surfaces such as artificial turf facilities (Janes et al. 2018), either as bound forms employed for the construction of tiles widely used in both outdoor and indoor safe surfaces such as playgrounds, schoolyards, nurseries, gym floors, and in urban pavements like walkways, tree protection or street furniture. However, several scientific studies have revealed the presence of hazardous compounds in the crumb rubber employed for the manufacture of recycled recreational surfaces. The presence of heavy metals has been reported (Bocca et al. 2009, Janes et al. 2018, Menichini et al. 2011), especially Cr, Cu, Ni, Pb and Zn at hundreds and even thousands of $\mu g\ g^{-1}$, then, exceeding the limits established by some regulations regarding the maximum concentration allowed in soils (Bocca et al. 2009). The presence of a high number of organic compounds, including polycyclic aromatic

hydrocarbons (PAHs), polychlorinated biphenyls (PCBs), paraffins, benzothiazoles, plasticizers, antioxidants, or phenols, among others have been also reported in the crumb rubber employed for playgrounds and synthetic turf pitches (Brandsma et al. 2019, Celeiro et al. 2014, Diekmann et al. 2019, Llompart et al. 2013, Schneider et al. 2020b). The presence of most of these hazardous compounds is expected in this recycled material, since most of the recycled rubber stems from shredded end-of-life tires, the main components of which are rubber polymers (up to 60%) and aromatic extender oils (up to 30%). Besides, the called 'carbon black', used as a reinforcing filler, is estimated to make up to 20 to 30 percent of every tire, and contains antioxidants, antiozonants and vulcanization agents (Diekmann et al. 2019).

The European Union (EU) applicable regulation for the crumb rubber is confusing, whereas the concern about the safety of this recycled material is increasing. As for the eight PAHs considered as carcinogenic by the ECHA (European Chemicals Agency): Benzo[a]pyrene (B[a]P), dibenzo[ah]anthracene (D[ah]A), benzo[e]pyrene (B[e]P), benzo[a]anthracene (B[a]A), chrysene (CHY), benzo[b]fluoranthene (B[b]F), benzo[j]fluoranthene (B[j]F), and benzo[k]fluoranthene (B[k]F) the European Commission restricts their contents to 1 μg g^{-1} in consumer goods and to 0.5 μg g^{-1} in materials 'with intensive contact' such as toys (JRC 2018, Off. J. Eur. Union 2013). Until now, the crumb rubber has been considered as a mixture. The concentration limits for PAHs in mixtures supplied to the general public have been set at 100 μg g^{-1} for B[a]P, and D[ah]A, and up to 1,000 μg g^{-1} for other 6 PAHs (B[e]P, B[a]A, CHY, B[b]F, B[j]F and B[k]F). Recently, the EU proposed the restriction of PAHs in granules and mulches used in synthetic turf pitches and playgrounds (2018a). This restriction intends to ensure that the cancer risk from exposure to the chemicals remains at a low level for those coming into contact, via inhalation and skin contact, with the crumb rubber. Several European

countries such as Netherlands, by the Dutch National Institute for Public Health and the Environment (RIVM), suggested a combined concentration limit of 17 µg g^{-1} for the eight ECHA PAHs (ECHA 2018) in these materials. On September 2019, based on this proposal and on the earlier opinion expressed by the Committee for Risk Assessment (RAC), the Committee for Socio-Economic Analysis (SEAC) adopted its final opinion: the restriction of the eight ECHA PAH total concentration to 20 µg g^{-1} in the granules and mulches used in synthetic turf pitches and playgrounds (ECHA 2019). Now, following the SEAC's final opinion, the European Commission will prepare a draft restriction measure to amend the REACH Restrictions list (Annex XVII) prior its entry into force (REACH).

In the United States, the Environmental Protection Agency (US EPA) and other agencies are also conducting studies to assess the potential human exposure of PAHs from tire crumb rubber employed as infill in synthetic turf sport facilities (EPA 2016). A study dealing with the identification of chemical compounds, and the human exposure to this material, has been recently published (EPA 2019). The study suggests exploring the feasibility of in-vitro studies to assess bioaccessibility and cytotoxicity, as well as in-vivo studies to evaluate the short-term toxicity effects from different exposure routes.

The primary route of human exposure is by dermal contact and oral intake (Diekmann et al. 2019), and recent studies suggest that the risk of cancer for children is 10 times higher if exposed to rubber surfaced playgrounds in comparison with uncovered surfaces (Tarafdar et al. 2019). In addition, the exposure of outdoor crumb rubber surfaces to different meteorological conditions favours the volatilization of these compounds which could be easily inhaled (Celeiro et al. 2018, Celeiro et al. 2014, Schneider et al. 2020a), or dragged by runoff water before reaching the sewage systems (urban pavements), or environmental waters (rubber recycled facilities close to rivers or lakes) (Celeiro et al.

2018, Celeiro et al. 2014, Diekmann et al. 2019). On the other hand, in last years, several green alternatives based on the use of cork or coconut crumb, are gaining interest to substitute the rubber infill, and several hybrid-natural sport surfaces are being tested with promising features.

Different extraction techniques have been reported for the analysis of PAHs, antioxidants or phenols in the crumb rubber (Li et al. 2010, Marsili et al. 2015). However, most of these techniques require several time-consuming steps and a high volume of organic solvents. A suitable option is the use of ultrasound-assisted extraction (UAE), a fast and reliable technique, followed by gas chromatography-tandem mass spectrometry (GC-MS/MS), which offers both a high sensitivity and selectivity to determine trace levels of the target compounds.

Therefore, this work aims at evaluating the presence of 42 hazardous compounds including 18 PAHs, 19 plasticizers (phthalates, adipates, and bisphenol A), 2 antioxidants and 3 acceleration and anti-degradants agents, in crumb rubber samples. Forty samples, including those collected from football pitches of synthetic turf and playgrounds, were considered. Besides, commercial tiles and crumb rubber, and urban pavers were analyzed to obtain a thorough characterization of a wide range of different rubber recycled surfaces, as well as car tires. In addition, a comparison between the crumb rubber and alternative green materials, such as cork crumb and sand, was performed.

2. EXPERIMENTAL

2.1. Reagents and materials

The studied compounds and their CAS numbers are summarized in **Table S1**. Ethyl acetate (EtAc) was provided by Sigma-Aldrich (Steinheim, Germany), methanol (MeOH) was supplied by Scharlab (Barcelona, Spain), and acetone was provided by Fluka Analytical (Steinheim, Germany).

Individual stock solutions of each compound were prepared in methanol or ethyl acetate. Further dilutions and mixtures were prepared in acetone (spike solutions) or ethyl acetate (calibration studies). Stock solutions were stored in glass vials protected from light at -20°C. All reagents were of analytical grade.

2.2 Sampling procedure

Forty samples from outdoor and indoor recreational surfaces, urban pavements, commercial rubber tiles, and car tires were analyzed. Besides, two alternative materials were included in this study. Details about the analyzed samples are given in **Table S2.**

The crumb rubber samples were directly collected from the studied surfaces in the region of Galicia (Northwest Spain). A similar number of crumb rubber samples from football pitches (13) and playgrounds (15) were collected. In the case of playgrounds, 10 were taken from outdoor playgrounds and 5 samples from indoor playing areas, since the number of indoor playgrounds is lower ~~in comparison with~~ than the outdoor ones, and the access to them~~se last facilities~~ is limited. To compare the composition of both synthetic turf football pitches and playgrounds with other recycled rubber ~~-~~materials, 4 samples came from urban pavements (tree protectors), and 3 commercial crumb rubber tiles, one of them employed as indoor gym floor, were also considered in this study. Besides, 2 commercial crumb rubber samples were marketed, and 3 car tires were acquired in local car workshops, since car tires are, a priori the material from which the crumb rubber come from. Regarding the alternative materials, cork crumb employed as infill in a football pitch, and sand employed as paver in an outdoor playground, were also collected and analyzed.

For the crumb rubber, cork and sand, between 2-100 g of sample were directly collected from the studied surfaces. For the tiles and car tires, samples were cut into small particles

(< 3mm). In all cases, samples were placed into a glass vial, sealed with an aluminum cap and stored at room temperature, and protected from light until their analysis took place.

2.3. Ultrasound Assisted Extraction (UAE)

Two hundred mg of the corresponding sample was placed in a 4 mL glass vial, and 2 mL of EtAc were added. Then, the vial was sealed with an aluminum cap furnished with PTFE-faced septum, and it was immersed into an ultrasound bath (P. Selecta, Barcelona, Spain) for 20 min, at 50 Hz and controlled temperature (25-30°C). After extraction, the organic supernatant was filtered through 0.22 µm PTFE filters (25 mm diameter), and diluted 1:10, v/v in EtAc prior the injection in the chromatographic system. The overall process comprised a sample dilution factor of 1:100 (w/v).

2.4. GC-MS/MS analysis

Analyses were carried out employing a Thermo Scientific Trace 1310 gas chromatograph coupled to a triple quadrupole mass spectrometer (TSQ 8000) with an autosampler IL 1310 from Thermo Scientific (San Jose, CA, USA). Separation was performed on a Zebron ZB-Semivolatiles column (30 m × 0.25 mm i.d. × 0.25 µm film thickness) obtained from Phenomenex (Torrance, CA, USA). Helium (purity 99.999%) was employed as carrier gas at a constant flow of 1.0 mL min^{-1}. The GC oven temperature was programmed from 60 °C (held 2 min) to 210 °C at 15°C min^{-1} and to 290 °C at 5°C min^{-1} (held 4 min). The total run time was 38 min. Pulsed splitless mode (200kPa, held 1.2 min) was employed for injection. The injector temperature was set at 270 °C, and the injection volume was 1 µL. The mass spectrometer detector (MSD) was operated in the electron ionization (EI) positive mode (+70 eV). The temperatures of the transfer line and the ion source were set at 290 °C, and 350 °C, respectively. The filament was set at 25 µA and the multiplier voltage was 1460 V. Selected Reaction Monitoring (SRM)

acquisition mode was implemented monitoring 2 or 3 transitions per compound (see **Table S1**) for an unequivocal identification and quantification of the target compounds. The system was operated by Xcalibur 2.2, and Trace Finder™ 3.2 software.

2.5. Chromatographic analysis

The 42 compounds determined in this work, including PAHs, plasticizers, antioxidants and vulcanizing additives are summarized in **Table S1**. The chromatographic conditions were optimized using a standard mixture prepared in ethyl acetate, achieving an efficient separation of most the target compounds (chromatographic conditions are described in Section 2.4).

The MS/MS working conditions were optimized using the semi-automated selected reaction monitoring (AutoSRM) tool implemented in the TSQ8000 GC–MS/MS software. For this purpose, individual standard solutions of each compound prepared in EtAc were employed. The AutoSRM process involves three steps: (i) precursor ion study; (ii) product ion study; and (iii) SRM optimization. ~~Thus, working in EI mode, the precursor ion was identified in the full scan (FS) mode for each compound. In a second step, the mass spectrometer was working in product ion scan mode and the most intense precursor ions were selected for subsequent fragmentation with different collision energies (CE) in the collision cell (Q2). Finally, the optimization of the CE for each transition was conducted, two or three transitions being selected. The most intense transition was used for quantification purposes, whereas the second and the third ones were employed for identification/confirmation purposes.~~ The experimental GC-MS/MS parameters including the retention times, the SRM transitions and CE for the studied compounds are summarized in **Table S1**. For some of the target compounds, the obtained MS/MS transitions were similar, but they can be successfully distinguished since they present different retention time. However, for two PAHs, B[b]F and B[j]F, both retention

time and MS/MS transitions are the same. Therefore, these compounds were quantified as sum in the analyzed samples.

2.6. UAE-GC-MS/MS performance

The UAE experimental parameters, including sample size, solvent type and volume, and microwave potency were previously optimized (Celeiro et al. 2018), demonstrating that the use of 200 mg of sample, 2 mL of EtAc and 50 Hz as UAE potency, offered the highest extraction efficiency.

Under the selected conditions, the UAE-GC-MS/MS method was validated in terms of linearity, accuracy, repeatability and reproducibility. Instrumental quantification limits (IQLs), and limits of quantification (LOQs) were also calculated. The method performance parameters are summarized in **Table S3**. Calibration standards were prepared in ethyl acetate covering a concentration range between 0.1 and 1000 µg L^{-1} for most compounds (see specific ranges in **Table S3**), including 13 concentration levels and three replicates per level. The method exhibited a direct proportional relationship between the amount of each analyte and its chromatographic response, obtaining coefficients of determination (R^2) higher than 0.9906 in all cases.

Instrumental method precision was evaluated within a day (n=3), and among days (n=6) for all the calibration concentration levels. Relative standard deviation (RSD) values for 10 µg L^{-1} (500 µg L^{-1} for DINP, DIDP, and 2MBTZ) are also shown in **Table S3**. In all cases, the RSD values were lower than 12% and 15% for repeteability and reproducibility, respectively.

Instrumental quantification limits (IQLs) were calculated as the compound concentration giving a signal-to-noise ratio of ten (S/N=10), employing standards containing low concentration of the target compounds prepared in EtAc. For two phthalates that were detected in the solvent blanks (DIBP and DEHP), IQLs were calculated as the

concentration corresponding to the signal of the blanks plus ten times its standard deviation. The limits of quantification (LOQs) in the samples were estimated considering the extraction dilution proccess (see details in Section 2.3) by multiplying 100 times the IQL values. They are shown in **Table S3**, and they were at the low ng g^{-1} level for all compounds, excluding the multiple phthalates DINP and DIDP, both mixture of branched chain isomers, and 2MTBZ, compound with a low sensitivity in GC analysis. Although samples were diluted 100 times prior analysis, as it was commented above, the method offered sufficient efficiency ~~enough~~ to ~~assure~~ ensure the ~~sensitive~~ analysis of these type of samples, since the limits required by the legislation are several orders of magnitude higher than those provided by the developed methodology. In any case, ~~if more~~should more sensitivity ~~were~~ required, the ratio of the UAE extract dilution could be lowered. However, in this case, an extract clean-up step would be neccessary.

To assess the accuracy of the proposed method, recovery studies were carried out employing two different crumb rubber real samples from a synthetic turf football pitch and from an outdoor playground. The study was performed at two concentration levels 1 µg g^{-1} and 10 µg g^{-1} for all compounds, excluding 3 of the 42 compounds: the phthalate mixtures DINP and DIDP, and 2-mercaptobenzothiazole (2MBTZ) (100 µg g^{-1}). The spiked samples were extracted and analyzed by triplicate. Since some of the target compounds were found in the non-spiked real samples, the initial concentrations were taken into account to calculate the recoveries. To the best of our knowledge, this is the first recovery and accuracy study performed in this type of recycled material.

As can be seen in **Table S3**, good accuracy and precision were achieved, with recovery values between 72 and 116 %, and RSD values lower than 15% in all cases.

3. RESULTS AND DISCUSSION

3.1. Analysis of the crumb rubber materials

Forty rubber samples from different recreational surfaces were analyzed following the UAE-GC-MS/MS procedure proposed in this study. Other rubber samples such as commercial tiles and crumb rubber, and scrap tires were also included. In addition, two green alternative materials (cork and sand) were analyzed. The description of the samples is given in **Table S2**.

3.1.1. Football pitches of synthetic turf

Thirteen crumb rubber samples from football pitches of synthetic turf (samples FP1-FP13, see **Table S2**) were analyzed. Besides, a cork sample (sample FP14), employed as infill in a football pitch was also analyzed for comparison purposes. Individual concentrations of the target compounds in the 13 analyzed samples are summarized in **Table S4**. Individual and total PAH contents in the synthetic turf football pitches, expressed in μg g^{-1}, are displayed in **Table 1.**

All samples contained PAHs, and their total concentration ranged between 8 μg g^{-1} and 95 μg g^{-1}. All the other target compounds, excluding D[ah]A, were found in the analyzed samples. Seven out of the 18 studied PAHs: PHEN, FLA, PYR, CHY, B[a]P, IND and B[ghi]P, were detected in all the samples, with relatively high concentrations of PYR up to 40 μg g^{-1}. The considered most potent carcinogenic PAH, B[a]P, was found in all samples, reaching concentrations ~~up to~~of 3.6 μg g^{-1}. The PAHs distribution per sample is depicted in **Fig. S1a.**

As can be seen, the profile was similar in all samples, with PYR contributing the most to the total PAH composition. This result, as well as the Σ PAHs levels agree with those reported in other studies (Celeiro et al. 2018, Diekmann et al. 2019, Han et al. 2008, Marsili et al. 2015, Schneider et al. 2020a). This includes the study of the National Dutch

Institute for Public Health and the Environment (RIVM), (RIVM 2017), where a median concentration of 5.8 µg g^{-1} for the 8 ECHA PAHs was reported, whereas in the present work, a median concentration of 6.0 µg g^{-1} was obtained for the 13 crumb rubber samples from synthetic turf football pitches.

Several authors observed a ~~decreasing~~ decrease of PAH concentrations in crumb rubber used for artificial turf due to ageing effects (Lioy et al. 2011, Marsili et al. 2015). However, this cannot be confirmed in the present study. The rubber granules are periodically refilled, and part of the rubber infill is dragged due to the continuous use of these sport surfaces (Celeiro et al. 2018, Han et al. 2008). Regarding the cork sample, only PHEN was found~~,~~ at a concentration up to two orders of magnitude lower than that found in the crumb rubber samples. The origin of this compound in the cork infill could be related with the fact that the football pitch was previously infilled with crumb rubber for a long time, and it is located in an intense traffic area. Thus, this green alternative may be a very suitable option for its use as infill in these type of sport surfaces, ~~concerning~~ as regards the absence of PAH exposure for users.

Individual concentrations of the other target compounds (plasticizers, antioxidants and vulcanization agents) are summarized in **Table 2**. Ten out of the 19 target plasticizers were found in the 13 analyzed samples. DBP, DEHA and DEHP were detected in all the crumb rubber samples at concentrations up to 32 µg g^{-1}. The other plasticizers were detected in 2-12 samples, reaching concentration levels ~~up~~ of~~to~~ 3.8 µg g^{-1}, excluding the multiple phthalate DIDP, that was detected at concentration higher than 87 µg g^{-1}. The antioxidant BHT was detected in all samples at concentrations up to 3.7 µg g^{-1}, whereas BTZ, 4TBP and 2MBTZ were found in 10, 9, and 3 samples, reaching concentrations ~~up~~ of~~to~~ 34, 4 and 62 µg g^{-1}, respectively. It is worth~~hy~~ ~~to mention~~ mentioning ~~than~~ that 2MBTZ is catalogued as a 2A group carcinogen, and as ~~a~~ substance of ~~very~~ high

concern (SVHC) by ECHA, considered as a moderate skin sensitizer, and very toxic to aquatic life with long-lasting effects (ECHA 2015). **Fig. S1b** exhibits the concentration of the detected plasticizers, antioxidants, and vulcanization agents in the analyzed crumb rubber samples from synthetic turf football pitches. In the cork sample, only DEP and BHT were found at low concentration (< 0.3 µg g^{-1}).

3.1.2. Playgrounds

Fifteen rubber samples from both outdoor (P1-P10) and indoor (P11-P15) playgrounds have been analyzed. Besides, a sand sample, employed as playground surface (P16), was included in the study. Individual and total concentration of the PAHs and the other target compounds are displayed in **Table 1** and **Table 2**, respectively (see **Table S5** for detailed results). The sand sample results were not included in the table, since none of the target compounds was detected.

All outdoor and indoor playground samples contained PAHs, being their total concentration between 1.0-6.0 µg g^{-1} and 9-25 µg g^{-1}, respectively. Three out of the 18 targeted, FLA, PYR and B[e]P, were found in all the analyzed outdoor samples at concentrations up to 2.9 µg g^{-1}, whereas in the indoor analyzed samples, 6 of them, PHEN, ANC, FLA, PYR, CHY, and B[ghi]P, were detected in all the samples, reaching concentrations up to 13 µg g^{-1}. The other PAHs were found in 10-80% of the analyzed samples, excluding D[ah]A that was only found in one indoor sample. The total PAH concentration was lower than those reported in studies performed several years ago (Diekmann et al. 2019, Lioy et al. 2011, Llompart et al. 2013). This can be attributed to the fact that the REACH regulation aimed at eliminating the use of so-called 'PAH-rich' extender oils in tires produced after January 2010 (Off J Eur Union 2015). This is resulting in an obvious reduction of PAH in crumb rubber, and a further decrease is expected since the called 'carbon black', used as a reinforcing filler (up to 30% of every

tire), was listed as a carcinogen by the International Agency for Research on Cancer (IARC). However, this ~~decrease in the~~ PAH~~s~~ concentration decrease was not observed in the crumb rubber employed as infill in synthetic turf football pitches, as it was in a previous study reported by the authors (Celeiro et al. 2018). This might suggest that the rubber material used for the construction of synthetic turf football pitches and playgrounds could come from different origins. Several authors observed that crumb rubber from non-EU tires, for which the REACH regulation (commented above) is not applicable (Off J Eur Union 2015), contained more PAHs than those from EU origin. In addition, these studies suggest that not only car tires are employed to obtain crumb rubber, other elastomeric materials like gaskets or brake tubes can be recycled as well, and used as infill in synthetic turf football pitches, increasing the PAH content (D.Fornai 2016, Diekmann et al. 2019). Nowadays, there are no regulations governing the declaration of the origin of rubber (previous use, country, age...) (Diekmann et al. 2019).

The PAH distribution profile for the analyzed playground samples is depicted in **Fig. S2a.** A comparison between the mean PAH concentrations ~~for~~ in crumb rubber from synthetic turf football pitches and playgrounds can be seen in **Fig. 1a**. The profile for playgrounds is slightly different from that obtained for the crumb rubber samples collected in ~~from~~ football pitches of synthetic turf. In this last case, PYR and FLA were the most important contributors to the total PAH content, with a difference up to two of magnitude order compared to the other detected PAHs. This behavior was also observed in the indoor playground samples. As regards the outdoor playgrounds, the PAH with the highest contribution to the total concentration was also PYR, followed in this case by CHY. ~~Also highlights the differences regarding~~ As regards the PAH~~s~~ profiles, ~~for the indoor playgrounds~~, ~~with a high concentration of~~ PYR, FLA and PHEN concentrations were~~,~~ up to 2 orders of magnitude higher in indoor playgrounds, than ~~those obtained~~ in ~~the~~ outdoor

playgrounds. However, ~~I~~in any case, the ~~mean~~ average PAH concentrations were clearly lower in both types of playgrounds in comparison with ~~the~~ those obtained in the football pitches.

Regarding plasticizers, 12 out of the 19 studied compounds were detected in the indoor samples and 10 of them in the outdoor playgrounds as it is depicted in **Fig. S2b**. The presence of the endocrine disruptor BPA, at concentration levels up to 4 μg g^{-1}, in 50% of the outdoor playgrounds and in all the indoor playgrounds should be underlined~~, at concentration levels up to 4 μg g^{-1}~~. The presence of DEHP in most samples, at concentration up to 46 μg g^{-1}, is also notable. However, these values, as well as those obtained for other phthalates such as DBP and DIBP are up to two orders of magnitude lower than the reported in indoor playgrounds and commercial pavers (Celeiro et al. 2014, Llompart et al. 2013) ~~construm~~manufactured prior the entry into force of ~~their~~the last phthalate restriction in plasticized materials (2018b). The higher phthalate~~s~~ concentration, especially ~~for~~those of ~~the multiple compounds~~ DINP and DIDP (concentrations levels of thousands of μg g^{-1} in an indoor shopping center playground)~~ as well as the presence of two of the multiple phthalates, DINP and DIDP, at concentrations levels of thousands of μg g^{-1} in an indoor shopping center playground~~. ~~(Celeiro et al. 2014, Llompart et al. 2013) (2018b).~~ ~~the multiple phthalates DINP and DIDP at concentrations up to 156 μg g^{-1}~~, and the fact that the crumb rubber material is more compacted in the indoor facilities than in ~~comparison with the~~ the outdoor one~~s~~s, might suggest that other plastic materials or other components such as glues and adhesives could have ~~be used~~been used to bind the material and to fix it on different surfaces.

BHT, BTZ and 4TBP were found in all the indoor samples~~,~~ and in several outdoor playground samples, at concentrations reaching ~~up to~~ 15 μg g^{-1}, whereas 2MBTZ was found at 190 μg g^{-1} in only one indoor sample. The indoor samples were collected from

Formatted: Not Superscript/ Subscript

Field Code Changed

Field Code Changed

shopping centers and airports, both very crowded places, where the main users of these surfaces are children and where hand-to-mouth contact is very frequent, favoring the entrance of the hazardous chemicals into the organism, together with the other routes (dermal and respiratory).

As regards the sand sample, although it was collected from a playground located within an intense traffic area, none of the target compounds was detected. Some authors relate the PAH content of this kind of recreational rubber surfaces with the emissions coming from urban traffic areas (Tarafdar et al. 2019). However, in this case, a porous material such as a sand surface appeared completely clear of contaminants, demonstrating its suitability as environmentally friendly and safe material to be used in playgrounds.

3.1.3. Urban surfaces, commercial tiles and crumb rubber, and scrap tires

Other crumb rubber samples from different origin were analyzed, including 4 urban surfaces employed as tree protectors (U1-U4), 3 commercial tiles (T1 and T2 were bought in the same local market, whereas T3 was on-line marketed, and it is currently being used as an indoor gym floor), and 2 commercial rubber granulates (R1, R2). Besides, 3 used car tires were analyzed (samples C1-C3). Detailed quantification results are shown in **Table S6. Table 3 and Table 4** summarize the total PAH and other target compound compositions, respectively.

Tree protectors

Thirteen target PAHs were detected in the four analyzed rubber tree protectors, reaching a total concentration of 18 μg g^{-1}. These urban surfaces, as well as the outdoor playgrounds and football pitches, are exposed to meteorological conditions (rain, temperature changes...) and, probably, for this reason, the presence of the most volatile PAHs (NAP, ACY, ACE) was not detected, as it is shown in **Fig. 1a**. However, for the

other PAHs, the profile for these urban pavements is similar than that observed indoor playgrounds.

Nine out of the 19 target plasticizers were found, highlighting the presence of the multiple phthalates DINP and DIDP, at hundreds and thousands of µg g^{-1} in several samples. BHT was found in two of the four analyzed samples, whereas BTZ and 4TBP were detected in all samples, reaching concentration of 18 µg g^{-1}.

Commercial rubber tiles

As can be seen in **Table 3**, all target PAHs were found in the three analyzed commercial rubber crumb tiles samples (T1-T3), highlighting the extremely high concentrations reached by PHEN and FLA, close to 1,000 µg g^{-1} in samples T1 and T2. Concentrations detected in sample T3, a pavement tile employed in an indoor gym flooring, were high but, in general, two orders of magnitude lower than in the other two samples. In this sample, the important contribution of PYR, FLA and CHY (sum, 57 µg g^{-1}) to the total PAH concentration (87 µg g^{-1}), must be highlighted. For samples T1 and T2, the total PAH content was higher than 5,600 µg g^{-1}. In these tile samples, 8 plasticizers were also detected, including DEHP, at concentrations up to 95 µg g^{-1}. The multiple phthalates DINP and DIDP were also found at concentrations of 153 µg g^{-1}. The other target compounds, BHT, BTZ and TBP were found in two samples, reaching concentrations of 7.2 µg g^{-1}. In general, the concentration range of plasticizers, antioxidants and vulcanization agents was similar to that observed in the indoor playgrounds.

Commercial crumb rubber

Two commercial crumb rubber samples were analyzed (R1-R2). 16 out of the 18 target PAHs were found, reaching a total concentration of 128 µg g^{-1}. The PAHs showing the highest concentration were PYR and FLA, being their contribution about 30% of the total

PAH content. These results agree with those reported on the total PAH content of recycled crumb rubber from European recyclers companies (Schneider et al. 2020b).

Although the PAH~~s~~ profile~~s~~ of these samples ~~is~~ are similar ~~than~~ to those obtained ~~from~~ in football pitches (see **Fig. 1a** and **Fig. 1b**), the mean concentrations ~~were~~ are clearly higher. Although only two commercial crumb rubber samples were analyzed in this study, these results are in concordance with those reported by Schneider et al. (Schneider et al. 2020a), who analyzed different crumb rubber samples obtained directly from recyclers companies. The mean concentration of PYR was 25 µg g^{-1}, similar to those found in the commercial crumb rubber samples included in this study (27 µg g^{-1}), and clearly higher than those ~~present~~ measured in the crumb rubber employed as infill in synthetic turf football pitches ~~analyzed in~~ of this study (12 µg g^{-1}).

Regarding plasticizers, nine were found at concentration up to 10 µg g^{-1}. Besides, the antioxidant BHT and the vulcanization agents BTZ and 4TBP were detected in the two crumb rubber samples, reaching concentrations of 20 µg g^{-1}.

Car tires

The analysis of three car tire samples (C1-C3) were included in ~~this~~ the present work. The target compound concentrations are summarized in **Table 4**. Fifteen out of the 18 target PAHs were detected, with PYR showing ~~in~~ the highest concentration in ~~all~~ the three samples with values up to 40 µg g^{-1}. The total PAH concentration were 100 µg g^{-1}, similar to those obtained for the commercial crumb rubber samples, but ~~very~~ much ~~low in comparison with~~ lower than those found in two of the commercial tiles that came from the same supplier. Regarding the mean PAH concentrations, as shown in **Fig. 1b**, these two commercial tiles ~~present~~ exhibit a completely different profile ~~in comparison~~compared with the commercial rubber granulates~~,~~ and car tires.

Eight plasticizers (DEP, DIBP, DBP, BPA, BBP, DEHA, DCHP and DEHP) were found in all samples, reaching concentration values of 91 μg g^{-1} for DEHP. The antioxidant BHT and the vulcanizing agents BTZ and 4TBP were also found in the three car tires, at low concentration (< 1 μg g^{-1}), excluding BTZ (13-70 μg g^{-1}).

3.4. Applicable legislation and future perspectives.

Until now, the crumb rubber material employed as infill in synthetic turf football pitches or children playgrounds and other recreational surfaces, has been considered as a mixture supplied to the general population. Therefore, the individual concentration limits for PAHs were set at 100 μg g^{-1} for B[a]P and D[ah]A, and at 1,000 μg g^{-1} for other six PAHs (B[e]P, B[a]A, CHY, B[b]F, B[j]F and B[k]F) (2018a). These maximum levels are disproportionately high, considering the intense use of these facilities, and taking into account the restricted levels for the eight ECHA PAHs in rubber consumer products that come into direct contact with the skin or the oral cavity (1 μg g^{-1}) or in toys (0.5 μg g^{-1}) (JRC 2018).

The users of the recycled rubber recreational surfaces are mainly children that have a frequent and direct contact with the crumb rubber material. Since PAHs are recognized carcinogenic compounds, the European Commission has recently~~,~~ (~~–~~September 2019)~~,~~ limited the total concentration of the 8 ECHA PAHs to 20 μg g^{-1} in granules and mulches used in synthetic turf pitches and playgrounds (ECHA 2019). This final opinion was adopted supporting the proposal of RIVM that suggested a combined concentration limit of 17 μg g^{-1} to address the risks from the eight ECHA PAHs (ECHA 2018). It is expected that in next months the final decision will be forwarded to the European Commission. If considered appropriate, a draft restriction action ~~measure~~ will be prepared to amend the REACH Restrictions list (Annex XVII) ~~will be prepared~~.

In addition, the ECHA is also progressing with its proposal to restrict the addition of microplastics to reduce the potential environmental risks. The granular infill material used in artificial turf pitches is understood to be an 'intentionally-added microplastic'. A public consultation on this proposal has been recently conducted to obtain the opinion of the RAC and SEAC, prior reaching a final decision and setting future restriction (ECHA 2019).

To easily compare the PAH contents in the crumb rubber samples coming from the different analyzed surfaces, **Fig. 2a** shows the Box-and-Whisker charts, which include the average, median and concentration range for the sum of eight ECHA and 16 EPA PAHs. As can be seen, the different recreational surfaces included in this study meet the recently proposed legal limit of 20 µg g^{-1} for the eight ECHA PAHs. Only two of the analyzed commercial tiles, both obtained from the same distributor, do not comply with this requirement. It is hard to explain the high PAHs concentration found in these two products, since car tires show considerably lower PAHs levels. It is possible that the crumb rubber come from a~~n entirely~~ different origin or/and include additional components than those typically employed in car tires. Although most of the other recycled rubber surfaces studied comply with the limit of 20 µg g^{-1} for the eight ECHA PAHs, this may be still a concern for children as they are the main users of these facilities. As such, the dermal absorption, inhalation and even ingestion of the crumb rubber suggest a likely high exposure. Therefore, further studies should be conducted to evaluate whether the proposed restriction is the most appropriate action to control the risks posed by the substances studied. Maybe this restriction should be tightened to be in concordance with the established maximum level in rubber consumer products (1 µg g^{-1}) or even in toys (0.5 µg g^{-1}) for the eight PAHs considered as carcinogenic by the ECHA (JRC 2018).

Fig. 3 shows Box-and-Whisker plots for three representative hazardous compounds in the various analyzed samples. B[a]P, which distribution is depicted in **Fig. 3a,** was selected since it is the most potent carcinogenic compound among the PAHs, and its concentration is a good indicator of the total carcinogenic potency of a PAH mixture (Hernández et al. 2019). In addition, since it is one of the eight ECHA PAHs, its maximum concentration in rubber consumer products is set to 1 μg g^{-1}, or 0.5 μg g^{-1} in toys. As can be seen, most of the studied surfaces meet ~~fulfill with~~ the limit of 20 μg g^{-1}, excluding again the two marketed tile samples supplied by the same distributor, with a concentration that clearly exceeds the limit set for rubber consumer products. **Fig. 3b** shows the Box-and-Whisker plot for DEHP. This compound is considered as an endocrine disruptor~~,~~ and its presence is restricted in toys, ~~and~~ childcare products and plasticis~~z~~ed material (2018b). As can be seen, car tires showed the highest DEHP concentrations, with values ranging from 18 to 91.5 μg g^{-1}. The active vulcanization agent BTZ may volatilize from crumb rubber and may provoke exposure by inhalation. In general, the highest concentration levels were also observed~~found~~ in the car tires followed by football pitches, indoor playgrounds, and tree protectors, as can be seen in **Fig. 3c**.

4. CONCLUSIONS

Forty crumb rubber samples coming from different sport, recreational and urban surfaces were analyzed by UAE-GC-MS/MS. Forty-two hazardous organic compounds such as PAHs, phthalates, adipates, antioxidants, and vulcanization agents were targeted. The results revealed the presence of 30 out of these 42 target compounds in the crumb rubber samples collected in synthetic turf football pitches and playgrounds, the Σ16 EPA PAHs ranging from 8 to 91 μg g^{-1}, and from 0.9 to 25 μg g^{-1}, respectively. The mean PAH concentrations were lower in the outdoor playgrounds ~~in comparison with~~than in the

indoor ones, and in any case, the concentrations in the two types of playgrounds were lower than those found in the football pitches samples. In general, the different crumb rubber recreational surfaces included in this study meet the recent proposed legal limit of 20 μg g^{-1} for the eight ECHA PAHs, excluding two of the analyzed commercial tiles coming from the same supplier that clearly exceed the legal limits. Further studies should be conducted to evaluate whether the proposed restriction is the most appropriate action to control the risks posed by these substances, especially for children. We suggest the present restriction should be tightened, to be in line with the maximum levels established in rubber consumer products intended to be in contact with skin, or in toys.

The analysis of alternative materials such as cork revealed the absence of PAHs and other compounds, thus offering a safe and sustainable alternative to crumb rubber for the manufacture of recreational or sport facilities.

Acknowledgements

This research was supported by projects RETOS PID2019-104336rb-100 (Ministry of Science and Innovation, Spain), and UNST10-1E-491 (Infrastructure Program, Ministry of Science and Innovation, Spain). The authors belong to the National Network for the Innovation in miniaturized sample preparation techniques, RED2018-102522-T (Ministry of Science, Innovation and Universities, Spain), to the Galician Competitive Research Group IN607B 2019/13, and ED431 2020/06 and to the CRETUS Strategic Partnership ED431 2018/01 (Xunta de Galicia). All these programs are co-funded by FEDER (UE).

Appendix A. Supplementary data

Supplementary data associated with this article can be found in the online version

Conflict of interest

The authors declare no conflict of interest

References

2018a. Annex XV restriction report proposal for a restriction substance name(s): eight polycyclic aromatic hydrocarbons (PAHs) in granules and mulches used as infill material in synthetic turf pitches and in loose form on playgrounds and in sport applications

2018b. Commission regulation (EU) 2018/2005 of 17 December 2018 amending Annex XVII to Regulation (EC) No 1907/2006 of the European Parliament and of the Council concerning the Registration, Evaluation, Authorisation and Restriction of Chemicals (REACH) as regards bis(2-ethylhexyl) phthalate (DEHP), dibutyl phthalate (DBP), benzyl butyl phthalate (BBP) and diisobutyl phthalate (DIBP) , L 322/14

Bocca B, Forte G, Petrucci F, Costantini S, Izzo P (2009) Metals contained and leached from rubber granulates used in synthetic turf areas. Sci Total Environ 407: 2183-2190

Brandsma SH, Brits M, Groenewoud QR, van Velzen MJM, Leonards PEG, De Boer J (2019) Chlorinated Paraffins in Car Tires Recycled to Rubber Granulates and Playground Tiles. Environ Sci Technol 53: 7595-7603

Celeiro M, Lamas JP, Garcia-Jares C, Dagnac T, Ramos L, Llompart M (2014) Investigation of PAH and other hazardous contaminant occurrence in recycled tyre rubber surfaces. Case-study: restaurant playground in an indoor shopping centre. Int J Env Anal Chem 94: 1264-1271

575 Celeiro M, Dagnac T, Llompart M (2018): Determination of priority and other hazardous
576 substances in football fields of synthetic turf by gas chromatography-mass spectrometry:
577 A health and environmental concern. Chemosphere 195: 201-211
578
579 Diekmann A, Giese U, Schaumann I (2019) Polycyclic aromatic hydrocarbons in
580 consumer goods made from recycled rubber material: A review. Chemosphere 220: 1163-
581 1178
582
583 Directive 2000/76/EC of the European Parliament and of the Council of 4 December 2000
584 on the incineration of waste. Off J Eur Union L.332
585
586 Directive 2000/53/EC of the European Parliament and of the Council of 18 September
587 2000 on end-of-life vehicles. Off J Eur Union L.269
588
589 ECHA (2015) Registered substance benzothiazole-2-thiol (2-MBT) Information of
590 Chemicals. Helsinki, Finland: European Chemicals Agency. http://
591 echa.europa.eu/information-on-chemicals. Accessed on April 2020
592
593 ECHA (2018) The Netherlands proposes a restriction on PAHs in granules and mulches
594 used as infill material. Public consultation.
595 https://echa.europa.eu/documents/10162/23665416/rest_rubber_granules_information_n
596 ote_12794_en.pdf/c18efa5f-3a93-5b9d-ea28-646462dc6a29. Accessed on April 2020
597
598 ECHA (2019) ECHA's scientific committees support restricting PAHs in granules and
599 mulches ECHA/PR/19/13. https://echa.europa.eu/-/echa-s-scientific-committees-
600 support-restricting-pahs-in-granules-and-mulches. Accessed April 2020
601
602 EPA (2016) Status Report: Federal Research Action Plan on Recycled Tire Crumb used
603 on playing fields and playground status report. https://www.epa.gov/chemical-

research/december-2016-status-report-federal-research-action-plan-recycled-tire-crumb-0. Accessed on April 2020

EPA (2019) July 2019 Report: Tire Crumb Rubber Characterization. https://www.epa.gov/chemical-research/july-2019-report-tire-crumb-rubber-characterization-0. Accessed on April 2020

Fornai D (2016) Characterization of rubber recycled from ELTs and assessment of the risks associated with dermal and inhalation exposure. Ecopneus

Han IK, Zhang L, Crain W (2008) Hazardous chemicals in synthetic turf materials and their bioaccessibility in digestive fluids. J Expo Sci Env Epid 18: 600-607

Hernández AF, Gil F, Tsatsakis AM, Gupta RC (2019): Chapter 33 - Biomarkers of Chemical Mixture Toxicity. In Gupta RC (ed) Biomarkers in Toxicology, 2nd edn. Elsevier, Academic Press,United Kingdom, pp 569-585

Janes C, Rodriguez L, Kelly C, White T, Beegan C (2018) A review of the potential risks associated with chemicals present in poured-in-place rubber surfacing. Environ Health Rev 61: 12-16

JRC (2018): Migration of Polycyclic Aromatic Hydrocarbons (PAHs) from plastic and rubber articles. Final report on the development of a migration measurement method https://publications.jrc.ec.europa.eu/repository/bitstream/JRC111476/kjna29282enn.pdf. Accessed on April 2020

Li X, Berger W, Musante C, Mattina MI (2010) Characterization of substances released from crumb rubber material used on artificial turf fields. Chemosphere 80: 279-285

633 Lioy P, Weisel C, Rinaldi MS, Stern A (2011) Crumb Infill and Turf Characterization for
634 Trace Elements and Organic Materials. Report prepared for NJDEP, Bureau of Recycling
635 and Planning https://www.nj.gov/dep/dsr/publications/turf-crumb-infill-study.pdf.
636 Accessed on April 2020
637
638 Llompart M, Sanchez-Prado L, Lamas JP, Garcia-Jares C, Roca E, Dagnac T (2013)
639 Hazardous organic chemicals in rubber recycled tire playgrounds and pavers.
640 Chemosphere 90: 423-431
641
642 Marsili L, Coppola D, Bianchi N, Maltese S, Bianchi M, Fossi MC (2015) Release of
643 polycyclic aromatic hydrocarbons and heavy metals from rubber crumb in synthetic turf
644 fields: preliminary hazard assessment for athletes. J Environ Anal Tox 5(2): 265-273
645
646 Menichini E, Abate V, Attias L, De Luca S, Di Domenico A, Fochi I, Forte G, Iacovella
647 N, Iamiceli AL, Izzo P (2011) Artificial-turf playing fields: contents of metals, PAHs,
648 PCBs, PCDDs and PCDFs, inhalation exposure to PAHs and related preliminary risk
649 assessment. Sci Total Environ 409: 4950-4957
650
651 Off J Eur Union 2013: Commission regulation (EU) No 1272/2013 of 6 December 2013
652 amending Annex XVII to Regulation (EC) No 1907/2006 of the European Parliament and
653 of the Council on the Registration, Evaluation, Authorisation and Restriction of
654 Chemicals (REACH) as regards polycyclic aromatic hydrocarbons (Text with EEA
655 relevance)
656
657 Off J Eur Union (2015): Commission regulation (EU) 2015/326 of 2 March 2015
658 amending Annex XVII to Regulation (EC) No 1907/2006 of the European Parliament and
659 of the Council on the Registration, Evaluation, Authorisation and Restriction of

Chemicals (REACH) as regards polycyclic aromatic hydrocarbons and phthalates (Text with EEA relevance)

REACH https://echa.europa.eu/substances-restricted-under-reach. Accessed on March 2020

RIVM (2017) Evaluation of health risks of playing sports on synthetic turf pitches with rubber granulate, RIVM Report 2017-0016

Schneider K, de Hoogd M, Haxaire P, Philipps A, Bierwisch A, Kaiser E (2020a) ERASSTRI-European Risk Assessment Study on Synthetic Turf Rubber Infill-Part 2: Migration and monitoring studies. Sci Total Environ 718: 137173

Schneider K, de Hoogd M, Madsen MP, Haxaire P, Bierwisch A, Kaiser E (2020b) ERASSTRI-European Risk Assessment Study on Synthetic Turf Rubber Infill-Part 1: Analysis of infill samples. Sci Total Environ 718: 137174

Sebola MR, Mativenga PT, Pretorius J (2018) A Benchmark study of waste tyre recycling in South Africa to European Union practice. Proc CIRP 69: 950-955

Tarafdar A, Oh MJ, Nguyen-Phuong Q, Kwon J- (2019) Profiling and potential cancer risk assessment on children exposed to PAHs in playground dust/soil: a comparative study on poured rubber surfaced and classical soil playgrounds in Seoul. Environ Geochem Health 42(6):1691-1704

Figure captions

Fig. 1 Mean PAH~~s~~ concentration~~s~~ obtained in **a)** football pitches, playgrounds and tree protectors and **b)** commercial crumb rubber, commercial tiles (values divided by 100), gym paver and car tires

689 **Fig. 2** Box-and-Whisker charts for **a)** Σ8 ECHA PAHs and **b)** Σ16 EPA PAHs in the
690 different analyzed recycled rubber samples. (Values divided by 1000 for the commercial
691 tiles)

692 **Fig. 3** Box-and-Whisker charts for some representative compounds **a)** B[a]P (values
693 divided by 100 for the commercial tiles), **b)** DEHP and **c)** BTZ in the different analyzed
694 recycled rubber samples

*Graphical Abstract

*Highlights (for review : 3 to 5 bullet points (maximum 85 characters including spaces per bullet point)

- 40 recycled rubber recreational and urban pavements (indoor/outdoor) were analyzed
- 42 chemicals including suspected carcinogens and endocrine disruptors were considered
- Sum of PAH concentrations at parts per million were found in all rubber surfaces
- Most samples fulfill the new EU regulation but exceed PAH limit in consumer products
- Green materials were free of hazardous compounds, then offering a safe alternative

Hazardous compounds in recreational and urban recycled surfaces made from crumb rubber. Compliance with current regulation and future perspectives

Maria Celeiro [1], Daniel Armada [1], Thierry Dagnac [2], Jacob de Boer [3], Maria Llompart [1*]

[1] CRETUS Institute, Department of Analytical Chemistry, Nutrition and Food Science, Universidade de Santiago de Compostela, E-15782, Santiago de Compostela, Spain.

[2] Agronomic Research Centre (AGACAL-CIAM) – Unit of Organic Contaminants, Apartado 10, E-15080, A Coruña, Spain.

[3] Department of Environment and Health (E&H), Vrije Universiteit, De Boelelaan 1085, 1081 HV, Amsterdam, Netherlands.

* Corresponding author: Maria Llompart (e-mail: maria.llompart@usc.es; telephone: +34881814225; fax: +34881814468)

ABSTRACT

Crumb rubber obtained from scrap tires is greatly employed for the construction of different facilities for sport, recreational and other uses. However, in recent years the concern about their safety and the related adult and children exposure to these surfaces is growing. This study aims a thorough chemical characterization encompassing 42 hazardous compounds, including polycyclic aromatic hydrocarbons (PAHs), phthalates, adipates, antioxidants and vulcanization agents in a wide range of crumb rubber from different surfaces. For the extraction of the target compounds, a method based on ultrasound-assisted extraction followed by gas chromatography-tandem mass spectrometry (UAE-GC-MS/MS) has been validated. Forty crumb rubber samples coming from synthetic turf football pitches, outdoor and indoor playgrounds, urban pavements, commercial tiles and granulates, and scrap tires, were analyzed. In addition, green alternative materials, such as sand and artificial turf based on cork granulate infill were included to compare the levels of the target compounds with those of crumb rubber. Most of the analyzed recycled surfaces meet the recent limits proposed by the European Commission for rubber granulates and mulches, although they exceed in several cases the maximum levels allowed for rubber consumer products. Besides, most of the other target

compounds, including several of them considered as endocrine disruptors, were detected in the analyzed samples, reaching parts per million concentrations.

KEYWORDS: Recycled rubber play surfaces; Public health; Polycyclic aromatic hydrocarbons, Hazardous organic compounds; Crumb rubber; Gas chromatography-tandem mass spectrometry

1. INTRODUCTION

The European Union (EU) is the second largest generator of scrap tires after United States, and according to the EU landfill and the end-of-life (EOL) vehicles directives, the national governments are obliged to address its recycling for safety, health and environmental purposes (Directive 2000/76/EC, Directive 2000/53/EC, Sebola et al. 2018).

The different processes and strategies proposed for the recycling of scrap (end-of-life) tires involve, among others, pyrolysis, controlled incineration, or mechanical crushing, the last one being the most employed one for its simplicity and low-cost. The obtained crumb rubber can be used in two different ways. Firstly, as infill in roads or sport surfaces such as artificial turf facilities (Janes et al. 2018), either as bound forms employed for the construction of tiles widely used in both outdoor and indoor safe surfaces such as playgrounds, schoolyards, nurseries, gym floors, and in urban pavements like walkways, tree protection or street furniture. However, several scientific studies have revealed the presence of hazardous compounds in the crumb rubber employed for the manufacture of recycled recreational surfaces. The presence of heavy metals has been reported (Bocca et al. 2009, Janes et al. 2018, Menichini et al. 2011), especially Cr, Cu, Ni, Pb and Zn at hundreds and even thousands of $\mu g\ g^{-1}$, then, exceeding the limits established by some regulations regarding the maximum concentration allowed in soils (Bocca et al. 2009). The presence of a high number of organic compounds, including polycyclic aromatic

hydrocarbons (PAHs), polychlorinated biphenyls (PCBs), paraffins, benzothiazoles, plasticizers, antioxidants, or phenols, among others have been also reported in the crumb rubber employed for playgrounds and synthetic turf pitches (Brandsma et al. 2019, Celeiro et al. 2014, Diekmann et al. 2019, Llompart et al. 2013, Schneider et al. 2020b). The presence of most of these hazardous compounds is expected in this recycled material, since most of the recycled rubber stems from shredded end-of-life tires, the main components of which are rubber polymers (up to 60%) and aromatic extender oils (up to 30%). Besides, the called 'carbon black', used as a reinforcing filler, is estimated to make up to 20 to 30 percent of every tire, and contains antioxidants, antiozonants and vulcanization agents (Diekmann et al. 2019).

The European Union (EU) applicable regulation for the crumb rubber is confusing, whereas the concern about the safety of this recycled material is increasing. As for the eight PAHs considered as carcinogenic by the ECHA (European Chemicals Agency): Benzo[a]pyrene (B[a]P), dibenzo[ah]anthracene (D[ah]A), benzo[e]pyrene (B[e]P), benzo[a]anthracene (B[a]A), chrysene (CHY), benzo[b]fluoranthene (B[b]F), benzo[j]fluoranthene (B[j]F), and benzo[k]fluoranthene (B[k]F) the European Commission restricts their contents to 1 μg g^{-1} in consumer goods and to 0.5 μg g^{-1} in materials 'with intensive contact' such as toys (JRC 2018, Off. J. Eur. Union 2013). Until now, the crumb rubber has been considered as a mixture. The concentration limits for PAHs in mixtures supplied to the general public have been set at 100 μg g^{-1} for B[a]P, and D[ah]A, and up to 1,000 μg g^{-1} for other 6 PAHs (B[e]P, B[a]A, CHY, B[b]F, B[j]F and B[k]F). Recently, the EU proposed the restriction of PAHs in granules and mulches used in synthetic turf pitches and playgrounds (2018a). This restriction intends to ensure that the cancer risk from exposure to the chemicals remains at a low level for those coming into contact, via inhalation and skin contact, with the crumb rubber. Several European

81 countries such as Netherlands, by the Dutch National Institute for Public Health and the
82 Environment (RIVM), suggested a combined concentration limit of 17 μg g^{-1} for the eight
83 ECHA PAHs (ECHA 2018) in these materials. On September 2019, based on this
84 proposal and on the earlier opinion expressed by the Committee for Risk Assessment
85 (RAC), the Committee for Socio-Economic Analysis (SEAC) adopted its final opinion:
86 the restriction of the eight ECHA PAH total concentration to 20 μg g^{-1} in the granules
87 and mulches used in synthetic turf pitches and playgrounds (ECHA 2019). Now,
88 following the SEAC's final opinion, the European Commission will prepare a draft
89 restriction measure to amend the REACH Restrictions list (Annex XVII) prior its entry
90 into force (REACH).
91 In the United States, the Environmental Protection Agency (US EPA) and other agencies
92 are also conducting studies to assess the potential human exposure of PAHs from tire
93 crumb rubber employed as infill in synthetic turf sport facilities (EPA 2016). A study
94 dealing with the identification of chemical compounds, and the human exposure to this
95 material, has been recently published (EPA 2019). The study suggests exploring the
96 feasibility of in-vitro studies to assess bioaccessibility and cytotoxicity, as well as in-vivo
97 studies to evaluate the short-term toxicity effects from different exposure routes.
98 The primary route of human exposure is by dermal contact and oral intake (Diekmann et
99 al. 2019), and recent studies suggest that the risk of cancer for children is 10 times higher
100 if exposed to rubber surfaced playgrounds in comparison with uncovered surfaces
101 (Tarafdar et al. 2019). In addition, the exposure of outdoor crumb rubber surfaces to
102 different meteorological conditions favours the volatilization of these compounds which
103 could be easily inhaled (Celeiro et al. 2018, Celeiro et al. 2014, Schneider et al. 2020a),
104 or dragged by runoff water before reaching the sewage systems (urban pavements), or
105 environmental waters (rubber recycled facilities close to rivers or lakes) (Celeiro et al.

2018, Celeiro et al. 2014, Diekmann et al. 2019). On the other hand, in last years, several green alternatives based on the use of cork or coconut crumb, are gaining interest to substitute the rubber infill, and several hybrid-natural sport surfaces are being tested with promising features.

Different extraction techniques have been reported for the analysis of PAHs, antioxidants or phenols in the crumb rubber (Li et al. 2010, Marsili et al. 2015). However, most of these techniques require several time-consuming steps and a high volume of organic solvents. A suitable option is the use of ultrasound-assisted extraction (UAE), a fast and reliable technique, followed by gas chromatography-tandem mass spectrometry (GC-MS/MS), which offers both a high sensitivity and selectivity to determine trace levels of the target compounds.

Therefore, this work aims at evaluating the presence of 42 hazardous compounds including 18 PAHs, 19 plasticizers (phthalates, adipates, and bisphenol A), 2 antioxidants and 3 acceleration and anti-degradants agents, in crumb rubber samples. Forty samples, including those collected from football pitches of synthetic turf and playgrounds, were considered. Besides, commercial tiles and crumb rubber, and urban pavers were analyzed to obtain a thorough characterization of a wide range of different rubber recycled surfaces, as well as car tires. In addition, a comparison between the crumb rubber and alternative green materials, such as cork crumb and sand, was performed.

2. EXPERIMENTAL

2.1. Reagents and materials

The studied compounds and their CAS numbers are summarized in **Table S1**. Ethyl acetate (EtAc) was provided by Sigma-Aldrich (Steinheim, Germany), methanol (MeOH) was supplied by Scharlab (Barcelona, Spain), and acetone was provided by Fluka Analytical (Steinheim, Germany).

Individual stock solutions of each compound were prepared in methanol or ethyl acetate. Further dilutions and mixtures were prepared in acetone (spike solutions) or ethyl acetate (calibration studies). Stock solutions were stored in glass vials protected from light at -20°C. All reagents were of analytical grade.

2.2 Sampling procedure

Forty samples from outdoor and indoor recreational surfaces, urban pavements, commercial rubber tiles, and car tires were analyzed. Besides, two alternative materials were included in this study. Details about the analyzed samples are given in **Table S2.**

The crumb rubber samples were directly collected from the studied surfaces in the region of Galicia (Northwest Spain). A similar number of crumb rubber samples from football pitches (13) and playgrounds (15) were collected. In the case of playgrounds, 10 were taken from outdoor playgrounds and 5 samples from indoor playing areas, since the number of indoor playgrounds is lower than the outdoor ones, and the access to them is limited. To compare the composition of both synthetic turf football pitches and playgrounds with other recycled rubber materials, 4 samples came from urban pavements (tree protectors), and 3 commercial crumb rubber tiles, one of them employed as indoor gym floor, were also considered in this study. Besides, 2 commercial crumb rubber samples were marketed, and 3 car tires were acquired in local car workshops, since car tires are, a priori the material from which the crumb rubber come from. Regarding the alternative materials, cork crumb employed as infill in a football pitch, and sand employed as paver in an outdoor playground, were also collected and analyzed.

For the crumb rubber, cork and sand, between 2-100 g of sample were directly collected from the studied surfaces. For the tiles and car tires, samples were cut into small particles (< 3mm). In all cases, samples were placed into a glass vial, sealed with an aluminum cap and stored at room temperature, and protected from light until their analysis took place.

2.3. Ultrasound Assisted Extraction (UAE)

Two hundred mg of the corresponding sample was placed in a 4 mL glass vial, and 2 mL of EtAc were added. Then, the vial was sealed with an aluminum cap furnished with PTFE-faced septum, and it was immersed into an ultrasound bath (P. Selecta, Barcelona, Spain) for 20 min, at 50 Hz and controlled temperature (25-30°C). After extraction, the organic supernatant was filtered through 0.22 µm PTFE filters (25 mm diameter), and diluted 1:10, v/v in EtAc prior the injection in the chromatographic system. The overall process comprised a sample dilution factor of 1:100 (w/v).

2.4. GC-MS/MS analysis

Analyses were carried out employing a Thermo Scientific Trace 1310 gas chromatograph coupled to a triple quadrupole mass spectrometer (TSQ 8000) with an autosampler IL 1310 from Thermo Scientific (San Jose, CA, USA). Separation was performed on a Zebron ZB-Semivolatiles column (30 m × 0.25 mm i.d. × 0.25 µm film thickness) obtained from Phenomenex (Torrance, CA, USA). Helium (purity 99.999%) was employed as carrier gas at a constant flow of 1.0 mL min^{-1}. The GC oven temperature was programmed from 60 °C (held 2 min) to 210 °C at 15°C min^{-1} and to 290 °C at 5°C min^{-1} (held 4 min). The total run time was 38 min. Pulsed splitless mode (200kPa, held 1.2 min) was employed for injection. The injector temperature was set at 270 °C, and the injection volume was 1 µL. The mass spectrometer detector (MSD) was operated in the electron ionization (EI) positive mode (+70 eV). The temperatures of the transfer line and the ion source were set at 290 °C, and 350 °C, respectively. The filament was set at 25 µA and the multiplier voltage was 1460 V. Selected Reaction Monitoring (SRM) acquisition mode was implemented monitoring 2 or 3 transitions per compound (see **Table S1**) for an unequivocal identification and quantification of the target compounds. The system was operated by Xcalibur 2.2, and Trace Finder™ 3.2 software.

2.5. Chromatographic analysis

The 42 compounds determined in this work, including PAHs, plasticizers, antioxidants and vulcanizing additives are summarized in **Table S1**. The chromatographic conditions were optimized using a standard mixture prepared in ethyl acetate, achieving an efficient separation of most the target compounds (chromatographic conditions are described in Section 2.4).

The MS/MS working conditions were optimized using the semi-automated selected reaction monitoring (AutoSRM) tool implemented in the TSQ8000 GC–MS/MS software. For this purpose, individual standard solutions of each compound prepared in EtAc were employed. The AutoSRM process involves three steps: (i) precursor ion study; (ii) product ion study; and (iii) SRM optimization. The experimental GC-MS/MS parameters including the retention times, the SRM transitions and CE for the studied compounds are summarized in **Table S1**. For some of the target compounds, the obtained MS/MS transitions were similar, but they can be successfully distinguished since they present different retention time. However, for two PAHs, B[b]F and B[j]F, both retention time and MS/MS transitions are the same. Therefore, these compounds were quantified as sum in the analyzed samples.

2.6. UAE-GC-MS/MS performance

The UAE experimental parameters, including sample size, solvent type and volume, and microwave potency were previously optimized (Celeiro et al. 2018), demonstrating that the use of 200 mg of sample, 2 mL of EtAc and 50 Hz as UAE potency, offered the highest extraction efficiency.

Under the selected conditions, the UAE-GC-MS/MS method was validated in terms of linearity, accuracy, repeatability and reproducibility. Instrumental quantification limits (IQLs), and limits of quantification (LOQs) were also calculated. The method

performance parameters are summarized in **Table S3**. Calibration standards were prepared in ethyl acetate covering a concentration range between 0.1 and 1000 µg L^{-1} for most compounds (see specific ranges in **Table S3**), including 13 concentration levels and three replicates per level. The method exhibited a direct proportional relationship between the amount of each analyte and its chromatographic response, obtaining coefficients of determination (R^2) higher than 0.9906 in all cases.

Instrumental method precision was evaluated within a day (n=3), and among days (n=6) for all the calibration concentration levels. Relative standard deviation (RSD) values for 10 µg L^{-1} (500 µg L^{-1} for DINP, DIDP, and 2MBTZ) are also shown in **Table S3**. In all cases, the RSD values were lower than 12% and 15% for repeteability and reproducibility, respectively.

Instrumental quantification limits (IQLs) were calculated as the compound concentration giving a signal-to-noise ratio of ten (S/N=10), employing standards containing low concentration of the target compounds prepared in EtAc. For two phthalates that were detected in the solvent blanks (DIBP and DEHP), IQLs were calculated as the concentration corresponding to the signal of the blanks plus ten times its standard deviation. The limits of quantification (LOQs) in the samples were estimated considering the extraction dilution proccess (see details in Section 2.3) by multiplying 100 times the IQL values. They are shown in **Table S3**, and they were at the low ng g^{-1} level for all compounds, excluding the multiple phthalates DINP and DIDP, both mixture of branched chain isomers, and 2MTBZ, compound with a low sensitivity in GC analysis. Although samples were diluted 100 times prior analysis, as it was commented above, the method offered sufficient efficiency to ensure the analysis of these type of samples, since the limits required by the legislation are several orders of magnitude higher than those provided by the developed methodology. In any case, should more sensitivityrequired,

231 the ratio of the UAE extract dilution could be lowered. However, in this case, an extract
232 clean-up step would be neccessary.
233 To assess the accuracy of the proposed method, recovery studies were carried out
234 employing two different crumb rubber real samples from a synthetic turf football pitch
235 and from an outdoor playground. The study was performed at two concentration levels 1
236 µg g^{-1} and 10 µg g^{-1} for all compounds, excluding 3 of the 42 compounds: the phthalate
237 mixtures DINP and DIDP, and 2-mercaptobenzothiazole (2MBTZ) (100 µg g^{-1}). The
238 spiked samples were extracted and analyzed by triplicate. Since some of the target
239 compounds were found in the non-spiked real samples, the initial concentrations were
240 taken into account to calculate the recoveries. To the best of our knowledge, this is the
241 first recovery and accuracy study performed in this type of recycled material.
242 As can be seen in **Table S3**, good accuracy and precision were achieved, with recovery
243 values between 72 and 116 %, and RSD values lower than 15% in all cases.
244
245
246 **3. RESULTS AND DISCUSSION**
247 **3.1. Analysis of the crumb rubber materials**
248 Forty rubber samples from different recreational surfaces were analyzed following the
249 UAE-GC-MS/MS procedure proposed in this study. Other rubber samples such as
250 commercial tiles and crumb rubber, and scrap tires were also included. In addition, two
251 green alternative materials (cork and sand) were analyzed. The description of the samples
252 is given in **Table S2**.
253 **3.1.1. Football pitches of synthetic turf**
254 Thirteen crumb rubber samples from football pitches of synthetic turf (samples FP1-
255 FP13, see **Table S2**) were analyzed. Besides, a cork sample (sample FP14), employed as

infill in a football pitch was also analyzed for comparison purposes. Individual concentrations of the target compounds in the 13 analyzed samples are summarized in **Table S4**. Individual and total PAH contents in the synthetic turf football pitches, expressed in μg g^{-1}, are displayed in **Table 1.**

All samples contained PAHs, and their total concentration ranged between 8 μg g^{-1} and 95 μg g^{-1}. All the other target compounds, excluding D[ah]A, were found in the analyzed samples. Seven out of the 18 studied PAHs: PHEN, FLA, PYR, CHY, B[a]P, IND and B[ghi]P, were detected in all the samples, with relatively high concentrations of PYR up to 40 μg g^{-1}. The considered most potent carcinogenic PAH, B[a]P, was found in all samples, reaching concentrations of 3.6 μg g^{-1}. The PAHs distribution per sample is depicted in **Fig. S1a.**

As can be seen, the profile was similar in all samples, with PYR contributing the most to the total PAH composition. This result, as well as the Σ PAHs levels agree with those reported in other studies (Celeiro et al. 2018, Diekmann et al. 2019, Han et al. 2008, Marsili et al. 2015, Schneider et al. 2020a). This includes the study of the National Dutch Institute for Public Health and the Environment (RIVM), (RIVM 2017), where a median concentration of 5.8 μg g^{-1} for the 8 ECHA PAHs was reported, whereas in the present work, a median concentration of 6.0 μg g^{-1} was obtained for the 13 crumb rubber samples from synthetic turf football pitches.

Several authors observed a decrease of PAH concentrations in crumb rubber used for artificial turf due to ageing effects (Lioy et al. 2011, Marsili et al. 2015). However, this cannot be confirmed in the present study. The rubber granules are periodically refilled, and part of the rubber infill is dragged due to the continuous use of these sport surfaces (Celeiro et al. 2018, Han et al. 2008). Regarding the cork sample, only PHEN was found at a concentration up to two orders of magnitude lower than that found in the crumb

281 rubber samples. The origin of this compound in the cork infill could be related with the
282 fact that the football pitch was previously infilled with crumb rubber for a long time, and
283 it is located in an intense traffic area. Thus, this green alternative may be a very suitable
284 option for its use as infill in these type of sport surfaces, as regards the absence of PAH
285 exposure for users.
286 Individual concentrations of the other target compounds (plasticizers, antioxidants and
287 vulcanization agents) are summarized in **Table 2**. Ten out of the 19 target plasticizers
288 were found in the 13 analyzed samples. DBP, DEHA and DEHP were detected in all the
289 crumb rubber samples at concentrations up to 32 μg g^{-1}. The other plasticizers were
290 detected in 2-12 samples, reaching concentration levels of 3.8 μg g^{-1}, excluding the
291 multiple phthalate DIDP, that was detected at concentration higher than 87 μg g^{-1}. The
292 antioxidant BHT was detected in all samples at concentrations up to 3.7 μg g^{-1}, whereas
293 BTZ, 4TBP and 2MBTZ were found in 10, 9, and 3 samples, reaching concentrations of
294 34, 4 and 62 μg g^{-1}, respectively. It is worth mentioning that 2MBTZ is catalogued as a
295 2A group carcinogen, and as a substance of very high concern (SVHC) by ECHA,
296 considered as a moderate skin sensitizer, and very toxic to aquatic life with long-lasting
297 effects (ECHA 2015). **Fig. S1b** exhibits the concentration of the detected plasticizers,
298 antioxidants, and vulcanization agents in the analyzed crumb rubber samples from
299 synthetic turf football pitches. In the cork sample, only DEP and BHT were found at low
300 concentration (< 0.3 μg g^{-1}).
301 **3.1.2. Playgrounds**
302 Fifteen rubber samples from both outdoor (P1-P10) and indoor (P11-P15) playgrounds
303 have been analyzed. Besides, a sand sample, employed as playground surface (P16), was
304 included in the study. Individual and total concentration of the PAHs and the other target
305 compounds are displayed in **Table 1** and **Table 2**, respectively (see **Table S5** for detailed

306 results). The sand sample results were not included in the table, since none of the target
307 compounds was detected.
308 All outdoor and indoor playground samples contained PAHs, being their total
309 concentration between 1.0-6.0 μg g^{-1} and 9-25 μg g^{-1}, respectively. Three out of the 18
310 targeted, FLA, PYR and B[e]P, were found in all the analyzed outdoor samples at
311 concentrations up to 2.9 μg g^{-1}, whereas in the indoor analyzed samples, 6 of them, PHEN,
312 ANC, FLA, PYR, CHY, and B[ghi]P, were detected in all the samples, reaching
313 concentrations up to 13 μg g^{-1}. The other PAHs were found in 10-80% of the analyzed
314 samples, excluding D[ah]A that was only found in one indoor sample. The total PAH
315 concentration was lower than those reported in studies performed several years ago
316 (Diekmann et al. 2019, Lioy et al. 2011, Llompart et al. 2013). This can be attributed to
317 the fact that the REACH regulation aimed at eliminating the use of so-called 'PAH-rich'
318 extender oils in tires produced after January 2010 (Off J Eur Union 2015). This is
319 resulting in an obvious reduction of PAH in crumb rubber, and a further decrease is
320 expected since the called 'carbon black', used as a reinforcing filler (up to 30% of every
321 tire), was listed as a carcinogen by the International Agency for Research on Cancer
322 (IARC). However, this PAH concentration decrease was not observed in the crumb rubber
323 employed as infill in synthetic turf football pitches, as it was in a previous study reported
324 by the authors (Celeiro et al. 2018). This might suggest that the rubber material used for
325 the construction of synthetic turf football pitches and playgrounds could come from
326 different origins. Several authors observed that crumb rubber from non-EU tires, for
327 which the REACH regulation (commented above) is not applicable (Off J Eur Union
328 2015), contained more PAHs than those from EU origin. In addition, these studies suggest
329 that not only car tires are employed to obtain crumb rubber, other elastomeric materials
330 like gaskets or brake tubes can be recycled as well, and used as infill in synthetic turf

331 football pitches, increasing the PAH content (D.Fornai 2016, Diekmann et al. 2019).
332 Nowadays, there are no regulations governing the declaration of the origin of rubber
333 (previous use, country, age...) (Diekmann et al. 2019).
334 The PAH distribution profile for the analyzed playground samples is depicted in **Fig. S2a.**
335 A comparison between the mean PAH concentrations in crumb rubber from synthetic turf
336 football pitches and playgrounds can be seen in **Fig. 1a**. The profile for playgrounds is
337 slightly different from that obtained for the crumb rubber samples collected in football
338 pitches of synthetic turf. In this last case, PYR and FLA were the most important
339 contributors to the total PAH content, with a difference up to two of magnitude order
340 compared to the other detected PAHs. This behavior was also observed in the indoor
341 playground samples. As regards the outdoor playgrounds, the PAH with the highest
342 contribution to the total concentration was also PYR, followed in this case by CHY. As
343 regards the PAH profiles, , PYR, FLA and PHEN concentrations were up to 2 orders of
344 magnitude higher in indoor playgrounds, than in outdoor playgrounds. However, in any
345 case, the average PAH concentrations were clearly lower in both types of playgrounds in
346 comparison with those obtained in the football pitches.
347 Regarding plasticizers, 12 out of the 19 studied compounds were detected in the indoor
348 samples and 10 of them in the outdoor playgrounds as it is depicted in **Fig. S2b**. The
349 presence of the endocrine disruptor BPA, at concentration levels up to 4 $\mu g\ g^{-1}$, in 50% of
350 the outdoor playgrounds and in all the indoor playgrounds should be underlined. The
351 presence of DEHP in most samples, at concentration up to 46 $\mu g\ g^{-1}$, is also notable.
352 However, these values, as well as those obtained for other phthalates such as DBP and
353 DIBP are up to two orders of magnitude lower than the reported in indoor playgrounds
354 and commercial pavers (Celeiro et al. 2014, Llompart et al. 2013) manufactured prior the
355 entry into force of the last phthalate restriction in plasticized materials (2018b). The

356 higher phthalate concentration, especially those of DINP and DIDP (concentrations levels
357 of thousands of μg g^{-1} in an indoor shopping center playground).
358 , and the fact that the crumb rubber material is more compacted in the indoor facilities
359 than in the outdoor ones, might suggest that other plastic materials or other components
360 such as glues and adhesives could have been used to bind the material and to fix it on
361 different surfaces.
362 BHT, BTZ and 4TBP were found in all the indoor samples and in several outdoor
363 playground samples, at concentrations reaching 15 μg g^{-1}, whereas 2MBTZ was found at
364 190 μg g^{-1} in only one indoor sample. The indoor samples were collected from shopping
365 centers and airports, both very crowded places, where the main users of these surfaces are
366 children and where hand-to-mouth contact is very frequent, favoring the entrance of the
367 hazardous chemicals into the organism, together with the other routes (dermal and
368 respiratory).
369 As regards the sand sample, although it was collected from a playground located within
370 an intense traffic area, none of the target compounds was detected. Some authors relate
371 the PAH content of this kind of recreational rubber surfaces with the emissions coming
372 from urban traffic areas (Tarafdar et al. 2019). However, in this case, a porous material
373 such as a sand surface appeared completely clear of contaminants, demonstrating its
374 suitability as environmentally friendly and safe material to be used in playgrounds.
375 **3.1.3. Urban surfaces, commercial tiles and crumb rubber, and scrap tires**
376 Other crumb rubber samples from different origin were analyzed, including 4 urban
377 surfaces employed as tree protectors (U1-U4), 3 commercial tiles (T1 and T2 were bought
378 in the same local market, whereas T3 was on-line marketed, and it is currently being used
379 as an indoor gym floor), and 2 commercial rubber granulates (R1, R2). Besides, 3 used
380 car tires were analyzed (samples C1-C3). Detailed quantification results are shown in

Table S6. Table 3 and Table 4 summarize the total PAH and other target compound compositions, respectively.

Tree protectors

Thirteen target PAHs were detected in the four analyzed rubber tree protectors, reaching a total concentration of 18 μg g^{-1}. These urban surfaces, as well as the outdoor playgrounds and football pitches, are exposed to meteorological conditions (rain, temperature changes...) and, probably for this reason, the presence of the most volatile PAHs (NAP, ACY, ACE) was not detected, as it is shown in **Fig. 1a**. However, for the other PAHs, the profile for these urban pavements is similar than that observed indoor playgrounds.

Nine out of the 19 target plasticizers were found, highlighting the presence of the multiple phthalates DINP and DIDP, at hundreds and thousands of μg g^{-1} in several samples. BHT was found in two of the four analyzed samples, whereas BTZ and 4TBP were detected in all samples, reaching concentration of 18 μg g^{-1}.

Commercial rubber tiles

As can be seen in **Table 3**, all target PAHs were found in the three analyzed commercial rubber crumb tile samples (T1-T3), highlighting the extremely high concentrations reached by PHEN and FLA, close to 1,000 μg g^{-1} in samples T1 and T2. Concentrations detected in sample T3, a pavement tile employed in an indoor gym flooring, were high but, in general, two orders of magnitude lower than in the other two samples. In this sample, the important contribution of PYR, FLA and CHY (sum, 57 μg g^{-1}) to the total PAH concentration (87 μg g^{-1}), must be highlighted. For samples T1 and T2, the total PAH content was higher than 5,600 μg g^{-1}. In these tile samples, 8 plasticizers were also detected, including DEHP at concentrations up to 95 μg g^{-1}. The multiple phthalates DINP and DIDP were also found at concentrations of 153 μg g^{-1}. The other target compounds,

406 BHT, BTZ and TBP were found in two samples, reaching concentrations of 7.2 μg g^{-1}. In
407 general, the concentration range of plasticizers, antioxidants and vulcanization agents was
408 similar to that observed in the indoor playgrounds.

409 ***Commercial crumb rubber***

410 Two commercial crumb rubber samples were analyzed (R1-R2). 16 out of the 18 target
411 PAHs were found, reaching a total concentration of 128 μg g^{-1}. The PAHs showing the
412 highest concentration were PYR and FLA, being their contribution about 30% of the total
413 PAH content. These results agree with those reported on the total PAH content of recycled
414 crumb rubber from European recyclers companies (Schneider et al. 2020b).

415 Although the PAH profiles of these samples are similar to those obtained in football
416 pitches (see **Fig. 1a** and **Fig. 1b**), the mean concentrations are clearly higher. Although
417 only two commercial crumb rubber samples were analyzed in this study, these results are
418 in concordance with those reported by Schneider et al. (Schneider et al. 2020a), who
419 analyzed different crumb rubber samples obtained directly from recyclers companies. The
420 mean concentration of PYR was 25 μg g^{-1}, similar to those found in the commercial crumb
421 rubber samples included in this study (27 μg g^{-1}), and clearly higher than those measured
422 in the crumb rubber employed as infill in synthetic turf football pitches of this study (12
423 μg g^{-1}).

424 Regarding plasticizers, nine were found at concentration up to 10 μg g^{-1}. Besides, the
425 antioxidant BHT and the vulcanization agents BTZ and 4TBP were detected in the two
426 crumb rubber samples, reaching concentrations of 20 μg g^{-1}.

427 ***Car tires***

428 The analysis of three car tire samples (C1-C3) were included in the present work. The
429 target compound concentrations are summarized in **Table 4**. Fifteen out of the 18 target
430 PAHs were detected, with PYR showing the highest concentration in the three samples

with values up to 40 μg g^{-1}. The total PAH concentration were 100 μg g^{-1}, similar to those obtained for the commercial crumb rubber samples, but much lower than those found in two of the commercial tiles that came from the same supplier. Regarding the mean PAH concentrations, as shown in **Fig. 1b**, these two commercial tiles exhibit a completely different profile compared with the commercial rubber granulates and car tires.

Eight plasticizers (DEP, DIBP, DBP, BPA, BBP, DEHA, DCHP and DEHP) were found in all samples, reaching concentration values of 91 μg g^{-1} for DEHP. The antioxidant BHT and the vulcanizing agents BTZ and 4TBP were also found in the three car tires, at low concentration (< 1 μg g^{-1}), excluding BTZ (13-70 μg g^{-1}).

3.4. Applicable legislation and future perspectives.

Until now, the crumb rubber material employed as infill in synthetic turf football pitches or children playgrounds and other recreational surfaces, has been considered as a mixture supplied to the general population. Therefore, the individual concentration limits for PAHs were set at 100 μg g^{-1} for B[a]P and D[ah]A, and at 1,000 μg g^{-1} for other six PAHs (B[e]P, B[a]A, CHY, B[b]F, B[j]F and B[k]F) (2018a). These maximum levels are disproportionately high, considering the intense use of these facilities, and taking into account the restricted levels for the eight ECHA PAHs in rubber consumer products that come into direct contact with the skin or the oral cavity (1 μg g^{-1}) or in toys (0.5 μg g^{-1}) (JRC 2018).

The users of the recycled rubber recreational surfaces are mainly children that have a frequent and direct contact with the crumb rubber material. Since PAHs are recognized carcinogenic compounds, the European Commission has recently (September 2019) limited the total concentration of the 8 ECHA PAHs to 20 μg g^{-1} in granules and mulches used in synthetic turf pitches and playgrounds (ECHA 2019). This final opinion was adopted supporting the proposal of RIVM that suggested a combined concentration limit

456 of 17 μg g^{-1} to address the risks from the eight ECHA PAHs (ECHA 2018). It is expected
457 that in next months the final decision will be forwarded to the European Commission. If
458 considered appropriate, a draft restriction action will be prepared to amend the REACH
459 Restrictions list (Annex XVII).
460 In addition, the ECHA is also progressing with its proposal to restrict the addition of
461 microplastics to reduce the potential environmental risks. The granular infill material used
462 in artificial turf pitches is understood to be an 'intentionally-added microplastic'. A public
463 consultation on this proposal has been recently conducted to obtain the opinion of the
464 RAC and SEAC, prior reaching a final decision and setting future restriction (ECHA
465 2019).
466 To easily compare the PAH contents in the crumb rubber samples coming from the
467 different analyzed surfaces, **Fig. 2a** shows the Box-and-Whisker charts, which include
468 the average, median and concentration range for the sum of eight ECHA and 16 EPA
469 PAHs. As can be seen, the different recreational surfaces included in this study meet the
470 recently proposed legal limit of 20 μg g^{-1} for the eight ECHA PAHs. Only two of the
471 analyzed commercial tiles, both obtained from the same distributor, do not comply with
472 this requirement. It is hard to explain the high PAHs concentration found in these two
473 products, since car tires show considerably lower PAHs levels. It is possible that the
474 crumb rubber come from a different origin or/and include additional components than
475 those typically employed in car tires. Although most of the other recycled rubber surfaces
476 studied comply with the limit of 20 μg g^{-1} for the eight ECHA PAHs, this may be still a
477 concern for children as they are the main users of these facilities. As such, the dermal
478 absorption, inhalation and even ingestion of the crumb rubber suggest a likely high
479 exposure. Therefore, further studies should be conducted to evaluate whether the
480 proposed restriction is the most appropriate action to control the risks posed by the

substances studied. Maybe this restriction should be tightened to be in concordance with the established maximum level in rubber consumer products (1 μg g^{-1}) or even in toys (0.5 μg g^{-1}) for the eight PAHs considered as carcinogenic by the ECHA (JRC 2018).

Fig. 3 shows Box-and-Whisker plots for three representative hazardous compounds in the various analyzed samples. B[a]P, which distribution is depicted in **Fig. 3a,** was selected since it is the most potent carcinogenic compound among the PAHs, and its concentration is a good indicator of the total carcinogenic potency of a PAH mixture (Hernández et al. 2019). In addition, since it is one of the eight ECHA PAHs, its maximum concentration in rubber consumer products is set to 1 μg g^{-1}, or 0.5 μg g^{-1} in toys. As can be seen, most of the studied surfaces meet the limit of 20 μg g^{-1}, excluding again the two marketed tile samples supplied by the same distributor, with a concentration that clearly exceeds the limit set for rubber consumer products. **Fig. 3b** shows the Box-and-Whisker plot for DEHP. This compound is considered as an endocrine disruptor and its presence is restricted in toys, childcare products and plasticized material (2018b). As can be seen, car tires showed the highest DEHP concentrations, with values ranging from 18 to 91.5 μg g^{-1}. The active vulcanization agent BTZ may volatilize from crumb rubber and may provoke exposure by inhalation. In general, the highest concentration levels were also observed in the car tires followed by football pitches, indoor playgrounds, and tree protectors, as can be seen in **Fig. 3c**.

4. CONCLUSIONS

Forty crumb rubber samples coming from different sport, recreational and urban surfaces were analyzed by UAE-GC-MS/MS. Forty-two hazardous organic compounds such as PAHs, phthalates, adipates, antioxidants, and vulcanization agents were targeted. The results revealed the presence of 30 out of these 42 target compounds in the crumb rubber

samples collected in synthetic turf football pitches and playgrounds, the Σ16 EPA PAHs ranging from 8 to 91 μg g^{-1}, and from 0.9 to 25 μg g^{-1}, respectively. The mean PAH concentrations were lower in the outdoor playgrounds than in the indoor ones, and in any case, the concentrations in the two types of playgrounds were lower than those found in the football pitch samples. In general, the different crumb rubber recreational surfaces included in this study meet the recent proposed legal limit of 20 μg g^{-1} for the eight ECHA PAHs, excluding two of the analyzed commercial tiles coming from the same supplier that clearly exceed the legal limits. Further studies should be conducted to evaluate whether the proposed restriction is the most appropriate action to control the risks posed by these substances, especially for children. We suggest the present restriction should be tightened to be in line with the maximum levels established in rubber consumer products intended to be in contact with skin, or in toys.

The analysis of alternative materials such as cork revealed the absence of PAHs and other compounds, thus offering a safe and sustainable alternative to crumb rubber for the manufacture of recreational or sport facilities.

Acknowledgements

This research was supported by projects RETOS PID2019-104336rb-100 (Ministry of Science and Innovation, Spain), and UNST10-1E-491 (Infrastructure Program, Ministry of Science and Innovation, Spain). The authors belong to the National Network for the Innovation in miniaturized sample preparation techniques, RED2018-102522-T (Ministry of Science, Innovation and Universities, Spain), to the Galician Competitive Research Group IN607B 2019/13 and ED431 2020/06 and to the CRETUS Strategic Partnership ED431 2018/01 (Xunta de Galicia). All these programs are co-funded by FEDER (UE).

Appendix A. Supplementary data

Supplementary data associated with this article can be found in the online version

Conflict of interest

The authors declare no conflict of interest

References

2018a. Annex XV restriction report proposal for a restriction substance name(s): eight polycyclic aromatic hydrocarbons (PAHs) in granules and mulches used as infill material in synthetic turf pitches and in loose form on playgrounds and in sport applications

2018b. Commission regulation (EU) 2018/2005 of 17 December 2018 amending Annex XVII to Regulation (EC) No 1907/2006 of the European Parliament and of the Council concerning the Registration, Evaluation, Authorisation and Restriction of Chemicals (REACH) as regards bis(2-ethylhexyl) phthalate (DEHP), dibutyl phthalate (DBP), benzyl butyl phthalate (BBP) and diisobutyl phthalate (DIBP) , L 322/14

Bocca B, Forte G, Petrucci F, Costantini S, Izzo P (2009) Metals contained and leached from rubber granulates used in synthetic turf areas. Sci Total Environ 407: 2183-2190

Brandsma SH, Brits M, Groenewoud QR, van Velzen MJM, Leonards PEG, De Boer J (2019) Chlorinated Paraffins in Car Tires Recycled to Rubber Granulates and Playground Tiles. Environ Sci Technol 53: 7595-7603

Celeiro M, Lamas JP, Garcia-Jares C, Dagnac T, Ramos L, Llompart M (2014) Investigation of PAH and other hazardous contaminant occurrence in recycled tyre rubber

surfaces. Case-study: restaurant playground in an indoor shopping centre. Int J Env Anal Chem 94: 1264-1271

Celeiro M, Dagnac T, Llompart M (2018): Determination of priority and other hazardous substances in football fields of synthetic turf by gas chromatography-mass spectrometry: A health and environmental concern. Chemosphere 195: 201-211

Diekmann A, Giese U, Schaumann I (2019) Polycyclic aromatic hydrocarbons in consumer goods made from recycled rubber material: A review. Chemosphere 220: 1163-1178

Directive 2000/76/EC of the European Parliament and of the Council of 4 December 2000 on the incineration of waste. Off J Eur Union L.332

Directive 2000/53/EC of the European Parliament and of the Council of 18 September 2000 on end-of-life vehicles. Off J Eur Union L.269

ECHA (2015) Registered substance benzothiazole-2-thiol (2-MBT) Information of Chemicals. Helsinki, Finland: European Chemicals Agency. http:// echa.europa.eu/information-on-chemicals. Accessed on April 2020

ECHA (2018) The Netherlands proposes a restriction on PAHs in granules and mulches used as infill material. Public consultation. https://echa.europa.eu/documents/10162/23665416/rest_rubber_granules_information_note_12794_en.pdf/c18efa5f-3a93-5b9d-ea28-646462dc6a29. Accessed on April 2020

ECHA (2019) ECHA's scientific committees support restricting PAHs in granules and mulches ECHA/PR/19/13. https://echa.europa.eu/-/echa-s-scientific-committees-support-restricting-pahs-in-granules-and-mulches. Accessed April 2020

EPA (2016) Status Report: Federal Research Action Plan on Recycled Tire Crumb used on playing fields and playground status report. https://www.epa.gov/chemical-research/december-2016-status-report-federal-research-action-plan-recycled-tire-crumb-0. Accessed on April 2020

EPA (2019) July 2019 Report: Tire Crumb Rubber Characterization. https://www.epa.gov/chemical-research/july-2019-report-tire-crumb-rubber-characterization-0. Accessed on April 2020

Fornai D (2016) Characterization of rubber recycled from ELTs and assessment of the risks associated with dermal and inhalation exposure. Ecopneus

Han IK, Zhang L, Crain W (2008) Hazardous chemicals in synthetic turf materials and their bioaccessibility in digestive fluids. J Expo Sci Env Epid 18: 600-607

Hernández AF, Gil F, Tsatsakis AM, Gupta RC (2019): Chapter 33 - Biomarkers of Chemical Mixture Toxicity. In Gupta RC (ed) Biomarkers in Toxicology, 2nd edn. Elsevier, Academic Press,United Kingdom, pp 569-585

Janes C, Rodriguez L, Kelly C, White T, Beegan C (2018) A review of the potential risks associated with chemicals present in poured-in-place rubber surfacing. Environ Health Rev 61: 12-16

JRC (2018): Migration of Polycyclic Aromatic Hydrocarbons (PAHs) from plastic and rubber articles. Final report on the development of a migration measurement method https://publications.jrc.ec.europa.eu/repository/bitstream/JRC111476/kjna29282enn.pdf. Accessed on April 2020

614 Li X, Berger W, Musante C, Mattina MI (2010) Characterization of substances released
615 from crumb rubber material used on artificial turf fields. Chemosphere 80: 279-285
616
617 Lioy P, Weisel C, Rinaldi MS, Stern A (2011) Crumb Infill and Turf Characterization for
618 Trace Elements and Organic Materials. Report prepared for NJDEP, Bureau of Recycling
619 and Planning https://www.nj.gov/dep/dsr/publications/turf-crumb-infill-study.pdf.
620 Accessed on April 2020
621
622 Llompart M, Sanchez-Prado L, Lamas JP, Garcia-Jares C, Roca E, Dagnac T (2013)
623 Hazardous organic chemicals in rubber recycled tire playgrounds and pavers.
624 Chemosphere 90: 423-431
625
626 Marsili L, Coppola D, Bianchi N, Maltese S, Bianchi M, Fossi MC (2015) Release of
627 polycyclic aromatic hydrocarbons and heavy metals from rubber crumb in synthetic turf
628 fields: preliminary hazard assessment for athletes. J Environ Anal Tox 5(2): 265-273
629
630 Menichini E, Abate V, Attias L, De Luca S, Di Domenico A, Fochi I, Forte G, Iacovella
631 N, Iamiceli AL, Izzo P (2011) Artificial-turf playing fields: contents of metals, PAHs,
632 PCBs, PCDDs and PCDFs, inhalation exposure to PAHs and related preliminary risk
633 assessment. Sci Total Environ 409: 4950-4957
634
635 Off J Eur Union 2013: Commission regulation (EU) No 1272/2013 of 6 December 2013
636 amending Annex XVII to Regulation (EC) No 1907/2006 of the European Parliament and
637 of the Council on the Registration, Evaluation, Authorisation and Restriction of
638 Chemicals (REACH) as regards polycyclic aromatic hydrocarbons (Text with EEA
639 relevance)
640

Off J Eur Union (2015): Commission regulation (EU) 2015/326 of 2 March 2015 amending Annex XVII to Regulation (EC) No 1907/2006 of the European Parliament and of the Council on the Registration, Evaluation, Authorisation and Restriction of Chemicals (REACH) as regards polycyclic aromatic hydrocarbons and phthalates (Text with EEA relevance)

REACH https://echa.europa.eu/substances-restricted-under-reach. Accessed on March 2020

RIVM (2017) Evaluation of health risks of playing sports on synthetic turf pitches with rubber granulate, RIVM Report 2017-0016

Schneider K, de Hoogd M, Haxaire P, Philipps A, Bierwisch A, Kaiser E (2020a) ERASSTRI-European Risk Assessment Study on Synthetic Turf Rubber Infill-Part 2: Migration and monitoring studies. Sci Total Environ 718: 137173

Schneider K, de Hoogd M, Madsen MP, Haxaire P, Bierwisch A, Kaiser E (2020b) ERASSTRI-European Risk Assessment Study on Synthetic Turf Rubber Infill-Part 1: Analysis of infill samples. Sci Total Environ 718: 137174

Sebola MR, Mativenga PT, Pretorius J (2018) A Benchmark study of waste tyre recycling in South Africa to European Union practice. Proc CIRP 69: 950-955

Tarafdar A, Oh MJ, Nguyen-Phuong Q, Kwon J- (2019) Profiling and potential cancer risk assessment on children exposed to PAHs in playground dust/soil: a comparative study on poured rubber surfaced and classical soil playgrounds in Seoul. Environ Geochem Health 42(6):1691-1704

669 **Figure captions**

670 **Fig. 1** Mean PAH concentrations obtained in **a)** football pitches, playgrounds and tree
671 protectors and **b)** commercial crumb rubber, commercial tiles (values divided by 100),
672 gym paver and car tires

673 **Fig. 2** Box-and-Whisker charts for **a)** Σ8 ECHA PAHs and **b)** Σ16 EPA PAHs in the
674 different analyzed recycled rubber samples. (Values divided by 1000 for the commercial
675 tiles)

676 **Fig. 3** Box-and-Whisker charts for some representative compounds **a)** B[a]P (values
677 divided by 100 for the commercial tiles), **b)** DEHP and **c)** BTZ in the different analyzed
678 recycled rubber samples

Figure 1

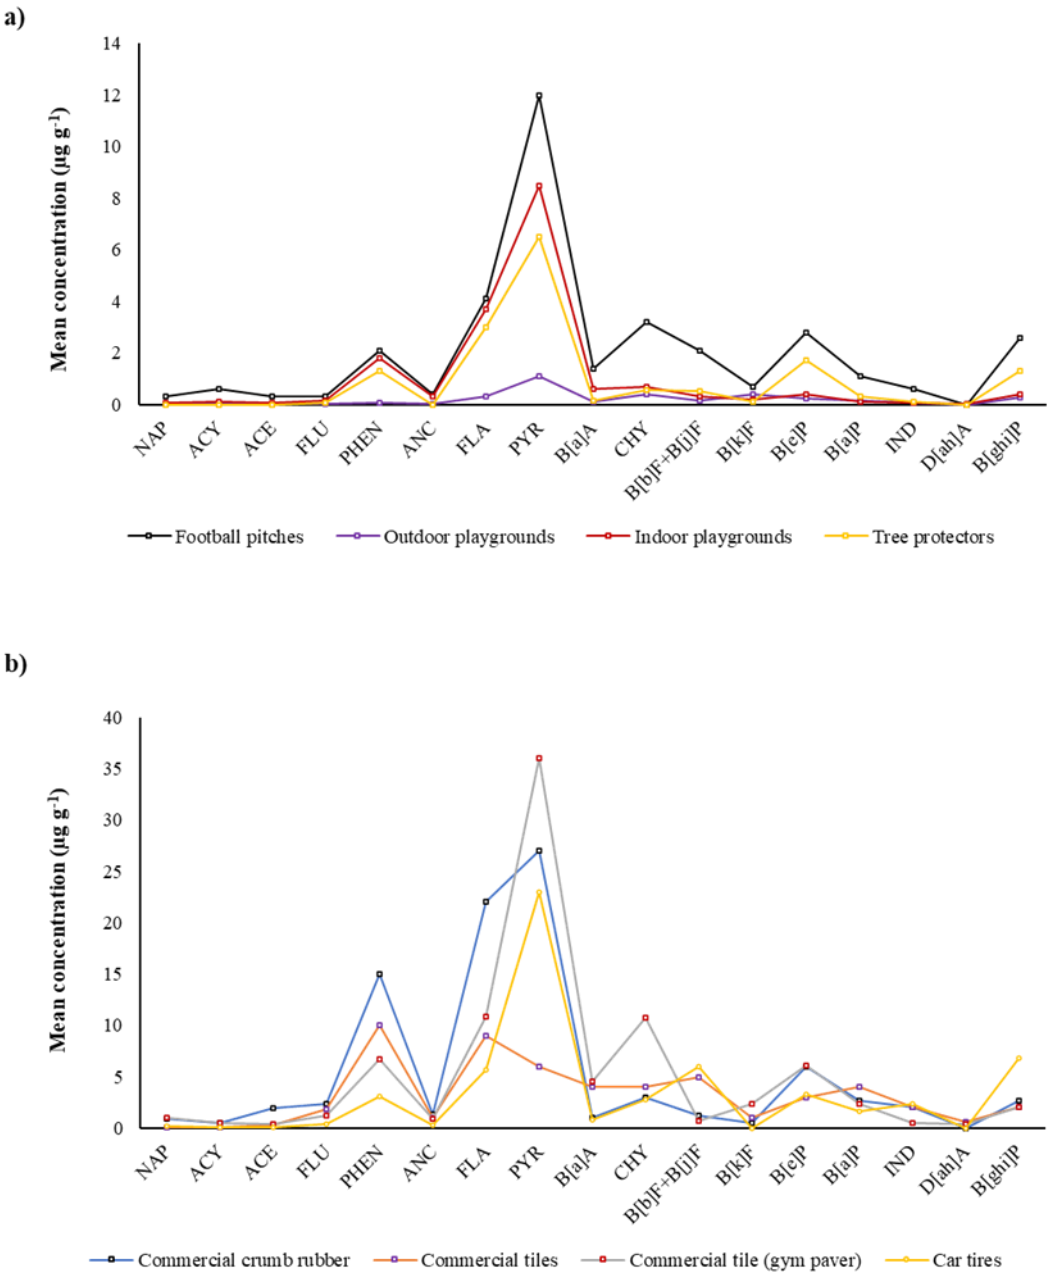

Figure 2

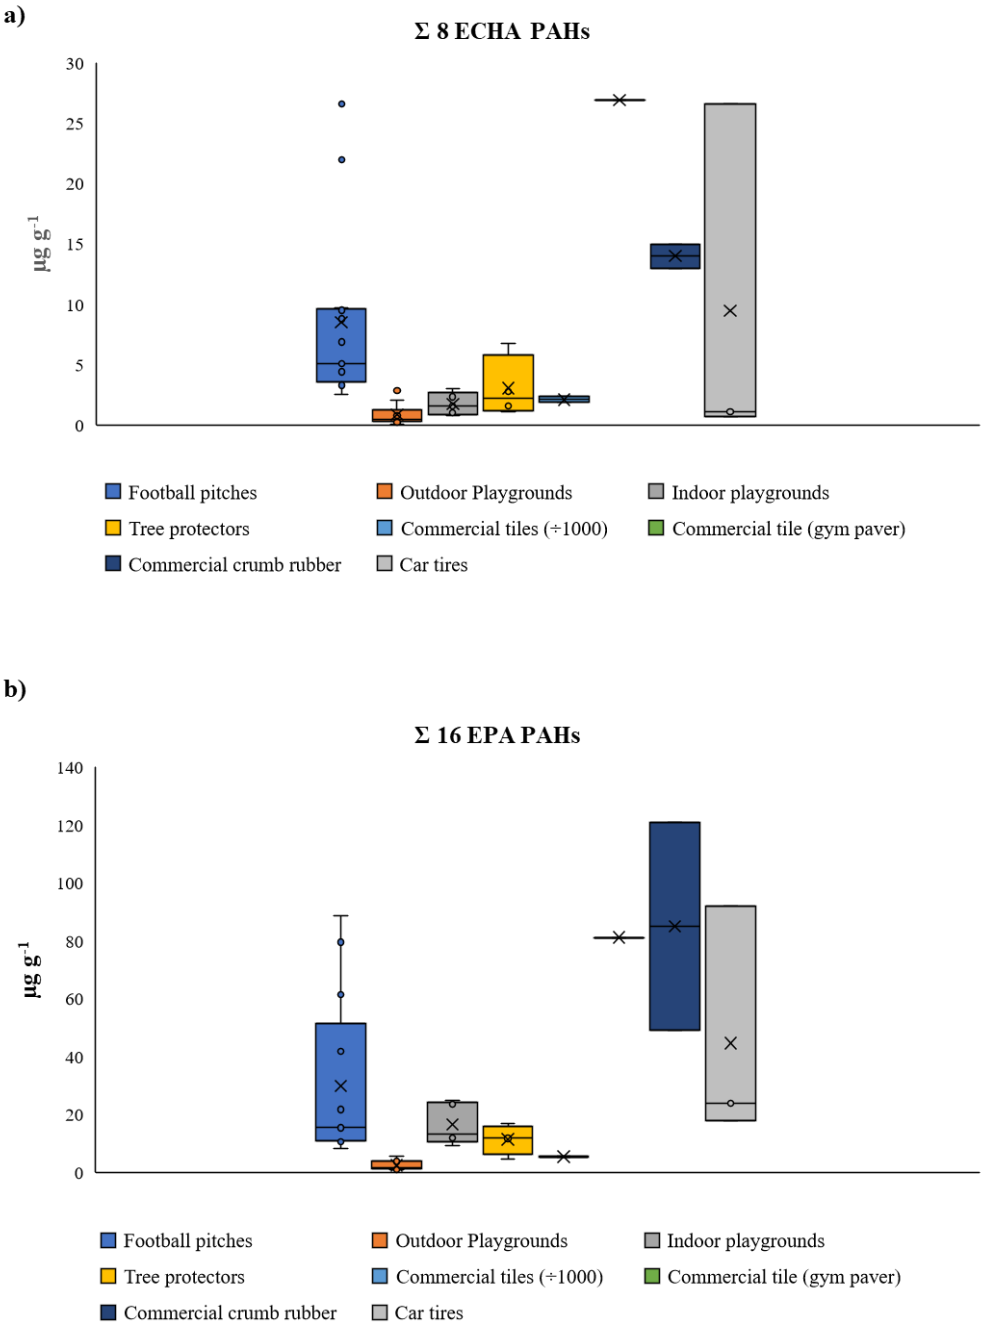
a)
Σ 8 ECHA PAHs
µg g-1
30
25
20
15
10
5
0
Football pitches
Outdoor Playgrounds
Indoor playgrounds
Tree protectors
Commercial tiles (÷1000)
Commercial tile (gym paver)
Commercial crumb rubber
Car tires
b)
Σ 16 EPA PAHs
µg g-1
140
120
100
80
60
40
20
0
Football pitches
Outdoor Playgrounds
Indoor playgrounds
Tree protectors
Commercial tiles (÷1000)
Commercial tile (gym paver)
Commercial crumb rubber
Car tires

Figure 3

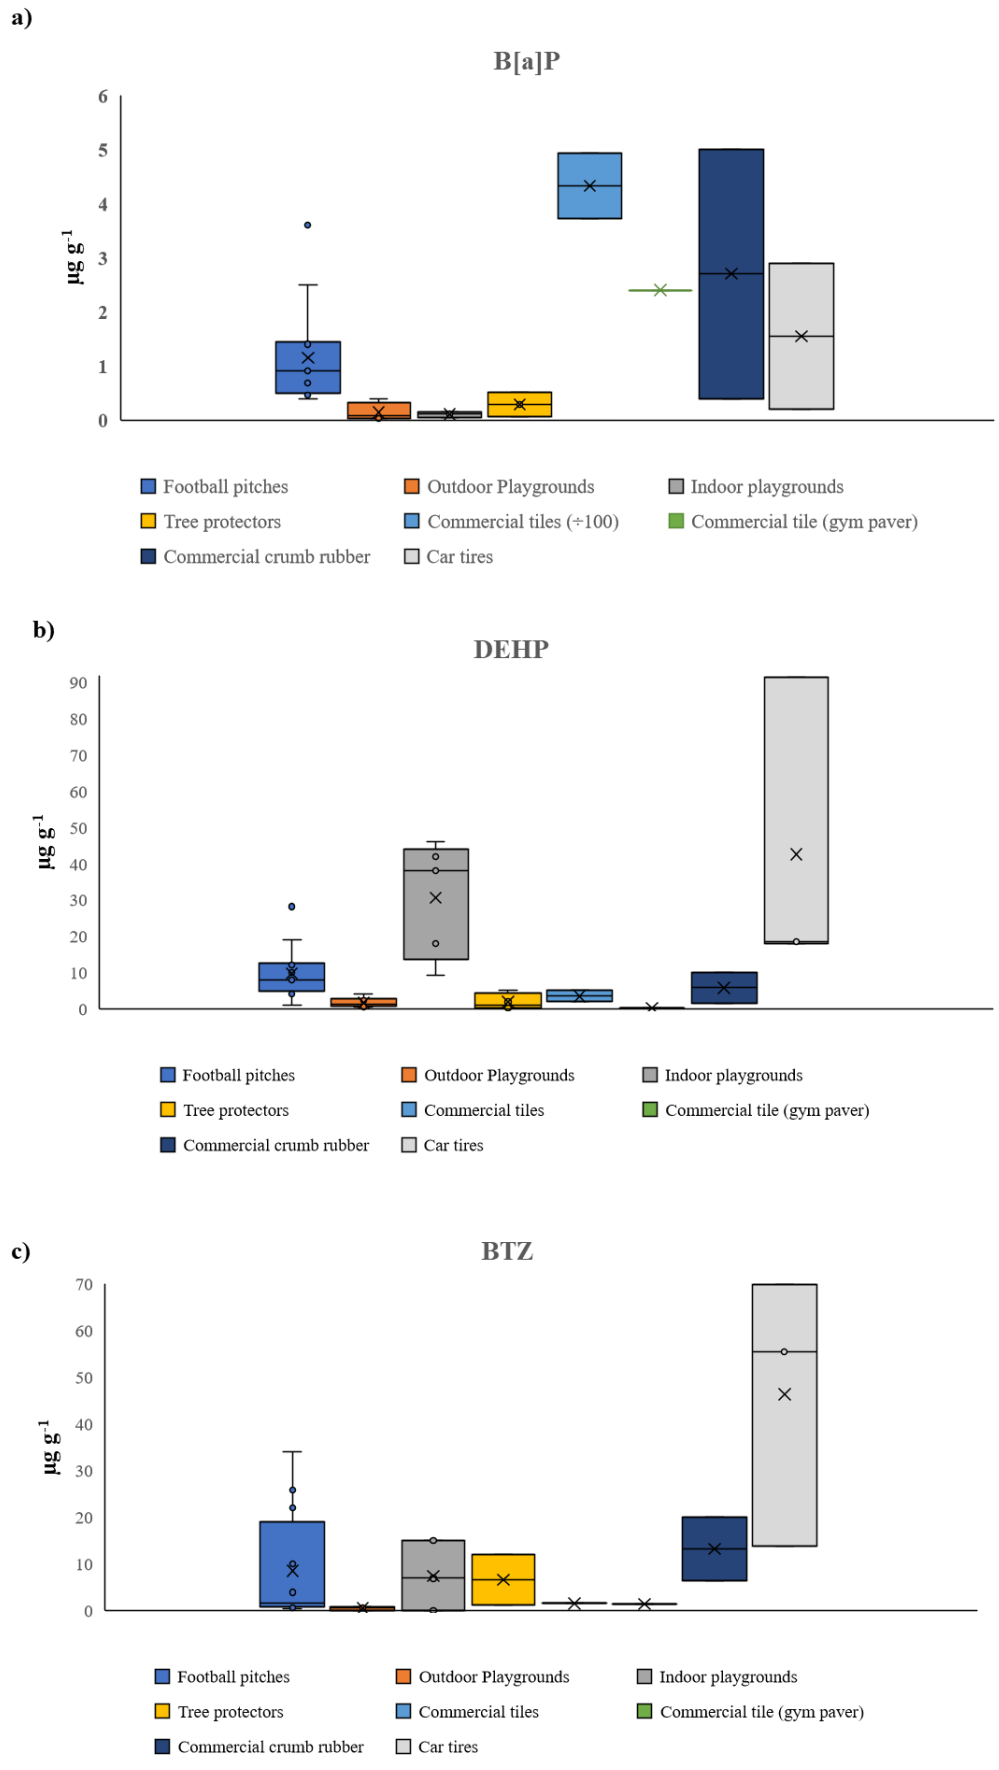
a)
B[a]P
µg g-1
0
1
2
3
4
5
6
Football pitches
Outdoor Playgrounds
Indoor playgrounds
Tree protectors
Commercial tiles (÷100)
Commercial tile (gym paver)
Commercial crumb rubber
Car tires
b)
DEHP
µg g-1
0
10
20
30
40
50
60
70
80
90
Football pitches
Outdoor Playgrounds
Indoor playgrounds
Tree protectors
Commercial tiles
Commercial tile (gym paver)
Commercial crumb rubber
Car tires
c)
BTZ
µg g-1
0
10
20
30
40
50
60
70
Football pitches
Outdoor Playgrounds
Indoor playgrounds
Tree protectors
Commercial tiles
Commercial tile (gym paver)
Commercial crumb rubber
Car tires

Table 1. PAHs concentration (μg g^{-1}) in the crumb rubber samples from synthetic turf football pitches and playgrounds.

	Football pitches of synthetic turf (FP1-FP13)				**Outdoor playgrounds (P1-P10)**				**Indoor playgrounds (P11-P15)**				**Cork (FP14)**
PAHs	**N [a] out of 13**	**Range**	**Average**	**Median**	**N [a] out of 10**	**Range**	**Average**	**Median**	**N [a] out of 5**	**Range**	**Average**	**Median**	**Average ± RSD**
NAP	12	0.04-0.90	0.3	0.1	2	0.012-0.017	0.014	0.014	3	0.03-0.09	0.05	0.04	
ACY	9	0.02-2.20	0.6	0.2	1	0.016	0.016	0.016	2	0.11-0.13	0.12	0.12	
ACE	3	0.08-0.61	0.3	0.3	1	0.012	0.011	0.011	1	0.05	0.05	0.05	
FLU	11	0.02-1.40	0.3	0.05	2	0.010-0.011	0.0105	0.0105	5	0.08-0.22	0.17	0.18	
PHEN	13	0.1-9.4	2.1	0.2	5	0.02-0.10	0.06	0.07	5	0.8-4.2	1.8	1.3	0.08 ± 0.01
ANC	10	0.01-1.60	0.4	0.1	5	0.01-0.10	0.04	0.03	4	0.07-0.88	0.3	0.2	
FLA	13	0.5-14	4.1	1.5	10	0.11-0.74	0.32	0.29	5	2.0-6.2	3.7	3.5	
PYR	13	0.8-40	12	4.3	10	0.2-2.9	1.1	1.0	5	4.9-13	8.5	6.6	
B[a]A	12	0.16-6.1	1.4	0.3	2	0.09-0.13	0.10	0.10	3	0.08-1.62	0.6	0.2	
CHY	13	1.4-7.5	3.2	2.6	9	0.1-1.2	0.4	0.3	5	0.4-1.3	0.7	0.6	
B[b]F+B[j]F	9	0.9-7.2	2.1	1.4	7	0.08-0.37	0.16	0.13	4	0.14-0.48	0.32	0.33	
B[k]F	11	0.1-2.0	0.7	0.6	2	0.06-0.8	0.42	0.42	4	0.02-0.55	0.18	0.07	
B[e]P	7	1.6-4.2	2.8	2.9	10	0.04-0.90	0.22	0.10	4	0.2-0.7	0.4	0.3	
B[a]P	13	0.4-3.6	1.1	0.9	4	0.02-0.42	0.14	0.07	3	0.05-0.16	0.10	0.11	
IND	13	0.3-1.6	0.6	0.5	4	0.05-0.14	0.08	0.07	2	0.04-0.10	0.07	0.07	
D[ah]A	0				0				1	0.03	0.03	0.03	
B[ghi]P	13	1.5-4.6	2.6	2.5	8	0.02-1.1	0.27	0.08	5	0.2-1.1	0.4	0.3	
Σ 8 ECHA PAHs	7	**3-30**	10	6	7	**0.1-3.1**	0.9	0.5	8	**0.8-3.3**	1.9	1.7	
Σ 16 EPA PAHs	15	**8-91**	32	16	15	**0.9-5.6**	2.5	1.7	16	**9-25**	17	13	**0.08 ± 0.01**
Σ Total PAHs	17	**8-95**	32	15	17	**1.0-6.0**	2.7	2.0	18	**9-25**	17	13	**0.08 ± 0.01**

[a] Number of samples out of the total containing the compounds

Table 2. Concentrations (µg g^{-1}) of plasticizers, antioxidants and vulcanization agents in the crumb rubber samples from synthetic turf football pitches and playgrounds.

Plasticizers	Football pitches of synthetic turf (FP1-FP13)				Outdoor playgrounds (P1-P10)				Indoor playgrounds (P11-15)				Cork (FP14)
	N [a] out of 13	Range	Average	Median	N [a] out of 10	Range	Average	Median	N [a] out of 5	Range	Average	Median	Average ± RSD
DMP	3	0.03-0.16	0.07	0.06	0				5	0.09-0.64	0.3	0.2	
DEP	9	0.04-0.70	0.2	0.1	5	0.01-1.00	0.3	0.3	5	0.5-3.3	2.0	2.1	0.04 ± 0.01
DIBP	12	0.2-3.8	1.4	1.0	7	0.1-10	1.7	0.3	5	2-84	29	16	
DBP	13	0.1-3.9	1.4	0.7	9	0.03-2.20	0.4	0.2	5	2-59	21	8	
BPA	9	0.06-1.30	0.5	0.3	5	0.05-4.50	1.4	0.6	5	0.08-4.00	1.7	2.1	0.27 ± 0.03
BBP	3	0.3-1.7	0.6	0.3	3	0.03-0.09	0.05	0.04	5	0.4-2.6	1.3	1.2	
DEHA	13	0.1-32	5.8	1.8	7	0.02-0.20	0.1	0.2	5	6.4-48	25	16	
DIHP	2	2.1-2.5	2.3	2.3	1	0.15	0.15	0.15	3	0.8-3.7	2.0	1.7	
DEHP	13	0.9-28	9.2	8.0	9	0.5-4.0	1.6	1.2	5	9-46	30	38	
DnOP	0				0				2	38-76	57	57	
DINP	0				2	84-92	88	88	3	34-2105	870	471	
DIDP	2	87-180	133	133	3	10-89	49	49	4	11-7331	1882	94	
Antioxidants and vulcanization agents													
BHT	13	0.06-3.70	1.1	1.0	6	0.01-0.30	0.1	0.1	5	0.2-0.9	0.5	0.6	0.18 ± 0.07
BTZ	10	0.6-34	9.1	2.7	2	0.6-0.8	0.7	0.7	4	1.8-15	12	15	
4TBP	9	0.05-4.10	1.8	1.3	3	0.03-0.51	0.3	0.3	5	0.2-1.2	0.6	0.6	
2MBTZ	3	29-62	43	39	0				1	190	190	190	

[a] Number of samples out of the total containing the compounds

Table 3. PAHs concentration (μg g^{-1}) in the crumb rubber samples from urban pavements (tree protectors), commercial rubber tiles and granulates, and car tires.

PAHs	Tree protectors (U1-U4)				Commercial products						Car tires (C1-C3)			
					Tiles (T1-T2)			Gym paver (T3)	Rubber granulates (R1-R2)					
	N [a] out of 4[a]	Range	Average	Median	N [a] out of 2	Range	Median	Average ± RSD	N [a] out of 2	Range	Median	N [a] out of 3	Range	Average	Median
NAP	0				2	4-6	5	1.15 ± 0.03	2	0.3-1.6	0.9	2	0.15-0.19	0.17	0.17
ACY	0				2	11-14	12	0.5 ± 0.1	2	0.4-0.8	0.5	3	0.07-0.12	0.10	0.11
ACE	0				2	27-31	29	0.4 ± 0.1	2	0.1-3.6	1.9	2	0.12-0.13	0.13	0.13
FLU	1	0.09	0.09	0.09	2	184-193	188	1.2 ± 0.3	2	0.4-4.4	2.4	3	0.1-0.5	0.4	0.5
PHEN	2	0.7-2.1	1.3	1.3	2	1043-1072	1057	6.7 ± 0.3	2	3.7-28	15	3	1.6-6.2	3.1	1.7
ANC	0				2	232-257	244	0.88 ± 0.05	2	0.6-2.1	1.3	3	0.1-0.5	0.3	0.4
FLA	2	2.1-3.9	3.0	3.0	2	928-997	962	10.9 ± 0.2	2	10-34	22	3	2.3-10	5.7	3.9
PYR	4	1-10	6.5	7.4	2	681-701	691	36 ± 2	2	24-31	27	3	12-40	23	16
B[a]A	4	0.1-0.2	0.15	0.14	2	405-484	444	4.5 ± 0.2	2	0.4-1.7	1.0	1	0.8	0.8	0.8
CHY	4	0.4-0.7	0.57	0.59	2	440-504	472	10.8 ± 0.3	2	1.2-4.8	3.0	3	0.3-7.9	2.8	0.3
B[b]F+B[j]F	4	0.2-1.0	0.52	0.39	2	442-562	502	0.68 ± 0.04	2	2.4-3.9	1.2	1	6.0	6.0	
B[k]F	3	0.04-0.17	0.13	0.13	2	110-155	132	2.4 ± 0.7	2	0.4-0.6	0.5	0			
B[e]P	4	0.3-5.0	1.7	0.7	2	273-350	311	6.1 ± 0.1	2	5-7	6.0	3	0.4-8.3	3.3	0.5
B[a]P	2	0.07-0.52	0.3	0.3	2	372-492	432	2.4 ± 0.6	2	0.4-5.4	2.7	2	0.2-2.9	1.6	1.6
IND	2	0.07-0.19	0.1	0.1	2	173-252	212	0.5 ± 0.1	2	0.2-3.8	2.0	1	2.4	2.4	2.4
D[ah]A	0				2	55-72	63	0.4 ± 0.1	0			0			
B[ghi]P	4	0.3-3.1	1.3	1.0	2	168-264	216	2.1 ± 0.3	2	1-4	2.7	2	1.2-12	6.8	6.8
Σ 8 ECHA PAHs		**1-7**	3.2	2.5	8	**2097-2619**	2353	**26**	7	**15-16**	16	5	**1-27**	9.5	1.1
Σ 16 EPA PAHs	10	**5-17**	12	12	16	**5117-5712**	5665	**82**	15	**51-123**	87	14	**18-92**	45	24
Σ Total PAHs	11	**6-18**	13	15	18	**5611-6343**	5977	**88**	17	**56-130**	93	16	**18-100**	48	24

[a] Number of samples out of the total containing the compounds

Table 4. Concentrations (μg g^{-1}) of plasticizers, antioxidants and vulcanization agents in the crumb rubber samples from urban pavements (tree protectors), commercial rubber tiles and granulates, and car tires.

Plasticizers	Tree protectors (U1-U4)				Commercial products						Car tires (C1-C3)			
					Tiles (T1-T2)			Gym paver (T3)	Rubber granulates (R1-R2)					
	N [a] out of 4	Range	Average	Median	N [a] out of 2	Range	Median	Average ± RSD	N [a] out of 2	Range	Median	N [a] out of 3	Range	Average	Median
DMP	0				0				2	0.03-0.09	0.06	0			
DEP	1	0.14	0.14	0.14	2	0.7-0.9	0.8	0.18 ± 0.04	2	0.06-0.24	0.15	3	0.4-0.9	0.6	0.5
DIBP	4	0.1-0.8	0.4	0.5	2	3.0-4.3	3.6	3.7 ± 0.2	2	1.2-2.1	1.6	3	2-19	12	15
DBP	4	0.1-1.5	0.5	0.3	2	4.1-4.8	4.4	4.5 ± 0.6	2	0.4-1.8	1.1	3	2-7	5	4
BPA	2	0.3-0.5	0.4	0.4	0				2	0.2-3.2	1.7	3	0.7-17	6.2	1.8
BBP	2	0.07-0.17	0.12	0.12	2	0.1-0.3	0.2	0.13 ± 0.02	2	0.1-0.4	0.2	3	0.4-1.8	0.9	0.4
DEHA	2	0.1-0.2	0.17	0.17	2	7.8-7.9	7.85	54 ± 8	2	1-9	5	3	10-56	27	14
DIHP	0				0				2	0.8-2.2	1.5				
DCHP	0				0				0			3	2-3	2.6	2.9
DEHP	4	0.9-5.1	2.6	2.2	2	62-95	78	12 ± 3	2	1-10	5	3	1-91	42	18
DINP	2	165-193	179	179	2	100-107	104	38 ± 3	0			0			
DIDP	2	440-1153	796	796	2	141-153	147	156 ± 35	0			0			
Antioxidants and vulcanization agents															
BHT	2	0.04-1.40	0.72	0.72	1	7.2	7.2	0.40 ± 0.02	2	0.6-1.4	1.0	3	0.2-0.4	0.3	0.3
BTZ	4	1.1-18	8.2	6.9	1	1.5	1.5	1.39 ± 0.04	2	6-20	13	3	13-70	46	56
4TBP	4	0.05-0.31	0.1	0.08	1	4.5	4.5	0.4 ± 0.1	2	3.0-3.9	3.4	3	0.2-0.7	0.5	0.7

[a] Number of samples out of the total containing the compounds

CRediT AUTHORS STATEMENTS

Maria Celeiro: Validation, formal analysis, investigation, writing-original draft, writing-review & editing, visualization.

Daniel Armada: Formal analysis, investigation, data curation.

Thierry Dagnac: conceptualization, writing-review & editing.

Jacob de Boer: conceptualization, writing-review & editing.

Maria Llompart: conceptualization, resources, writing-review & editing, supervision, project administration, funding acquisition.

*Declaration of Interest Statement

Declaration of interests

☒ The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

☐The authors declare the following financial interests/personal relationships which may be considered as potential competing interests: